

8-25-2010

Interplay of Fe and Nd magnetism in NdFeAsO single crystals

W. Tian

Iowa State University

W. Ratcliff II

National Institute of Standards and Technology

M. G. Kim

Iowa State University

J.-Q. Yan

Iowa State University

P. A. Klenzle

National Institute of Standards and Technology

Follow this and additional works at: http://lib.dr.iastate.edu/ameslab_pubs



Part of the [Condensed Matter Physics Commons](#), and the [Materials Science and Engineering Commons](#)

The complete bibliographic information for this item can be found at http://lib.dr.iastate.edu/ameslab_pubs/46. For information on how to cite this item, please visit <http://lib.dr.iastate.edu/howtocite.html>.

This Article is brought to you for free and open access by the Ames Laboratory at Iowa State University Digital Repository. It has been accepted for inclusion in Ames Laboratory Publications by an authorized administrator of Iowa State University Digital Repository. For more information, please contact digirep@iastate.edu.

Interplay of Fe and Nd magnetism in NdFeAsO single crystals

Abstract

The structural and magnetic phase transitions have been studied on NdFeAsO single crystals by neutron and x-ray diffraction complemented by resistivity and specific-heat measurements. Two low-temperature phase transitions have been observed in addition to the tetragonal-to-orthorhombic transition at $T_S \sim 142$ K and the onset of antiferromagnetic (AFM) Fe order below $T_N \sim 137$ K. The Fe moments order AFM in the well-known stripelike structure in the (ab) plane but change from AFM to ferromagnetic (FM) arrangement along the c direction below $T^* \sim 15$ K accompanied by the onset of Nd AFM order below $T_{Nd} \sim 6$ K with this same AFM configuration. The iron magnetic order-order transition in NdFeAsO accentuates the Nd-Fe interaction and the delicate balance of c-axis exchange couplings that results in AFM in LaFeAsO and FM in CeFeAsO and PrFeAsO.

Keywords

Physics and Astronomy, Materials Science and Engineering

Disciplines

Condensed Matter Physics | Materials Science and Engineering

Comments

This article is from *Physical Review B* 82 (2010): 060514(R), doi:[10.1103/PhysRevB.82.060514](https://doi.org/10.1103/PhysRevB.82.060514).

Authors

W. Tian, W. Ratcliff II, M. G. Kim, J.-Q. Yan, P. A. Klenzle, Q. Huang, Brandt A. Jensen, Kevin W. Dennis, R. William McCallum, Thomas A. Lograsso, Robert J. McQueeney, Alan I. Goldman, J. W. Lynn, and Andreas Kreyssig



Interplay of Fe and Nd magnetism in NdFeAsO single crystals

W. Tian,¹ W. Ratcliff II,² M. G. Kim,^{1,3} J.-Q. Yan,¹ P. A. Kienzle,² Q. Huang,² B. Jensen,¹ K. W. Dennis,¹ R. W. McCallum,^{1,4}
T. A. Lograsso,¹ R. J. McQueeney,^{1,3} A. I. Goldman,^{1,3} J. W. Lynn,² and A. Kreyssig^{1,3}

¹Ames Laboratory, Ames, Iowa 50011, USA

²NIST Center for Neutron Research, National Institute of Standards and Technology, Gaithersburg, Maryland 20899, USA

³Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA

⁴Department of Materials Science and Engineering, Iowa State University, Ames, Iowa 50011, USA

(Received 6 June 2010; revised manuscript received 9 August 2010; published 25 August 2010)

The structural and magnetic phase transitions have been studied on NdFeAsO single crystals by neutron and x-ray diffraction complemented by resistivity and specific-heat measurements. Two low-temperature phase transitions have been observed in addition to the tetragonal-to-orthorhombic transition at $T_S \sim 142$ K and the onset of antiferromagnetic (AFM) Fe order below $T_N \sim 137$ K. The Fe moments order AFM in the well-known stripelike structure in the (*ab*) plane but change from AFM to ferromagnetic (FM) arrangement along the *c* direction below $T^* \sim 15$ K accompanied by the onset of Nd AFM order below $T_{Nd} \sim 6$ K with this same AFM configuration. The iron magnetic order-order transition in NdFeAsO accentuates the Nd-Fe interaction and the delicate balance of *c*-axis exchange couplings that results in AFM in LaFeAsO and FM in CeFeAsO and PrFeAsO.

DOI: [10.1103/PhysRevB.82.060514](https://doi.org/10.1103/PhysRevB.82.060514)

PACS number(s): 74.70.Xa, 75.25.-j, 61.50.Ks, 75.30.Kz

Since the discovery of high-temperature superconductivity in the fluorine-doped compound LaFeAsO_{1-x}F_x with a superconducting transition temperature of $T_c = 26$ K,¹ enormous efforts have been made to understand the crystallographic, magnetic, and superconducting properties of the RFeAsO compounds (*R*=rare-earth elements) and their doped superconducting derivatives with T_c 's up to ~ 55 K.²⁻¹⁸ The parent RFeAsO compounds undergo a tetragonal-to-orthorhombic phase transition and show antiferromagnetic (AFM) order of Fe and *R* moments.^{2,12-18} Although doping suppresses both the lattice distortion and Fe magnetic order, magnetism is believed to play a major role in the superconducting pairing mechanism in pnictide superconductors demonstrated, e.g., by the observation of a magnetic resonance in the superconducting state.¹⁹ Detailed knowledge of the magnetic order and crystallographic structure is a key to gain insight into the magnetic and magneto-elastic coupling but has been hampered, so far, by the absence of sizeable RFeAsO single crystals.

Here we report on a neutron and x-ray diffraction study of recently available²⁰ NdFeAsO single crystals complemented by resistivity and specific-heat measurements. In prior neutron powder studies, the tetragonal-to-orthorhombic lattice distortion has been observed below $T_S \sim 150$ K (Ref. 13) followed by the onset of the well-known stripelike AFM order of Fe below $T_N \sim 141$ K.¹² The onset of the Nd AFM order was reported for temperatures below $T_{Nd} \sim 2$ K in neutron powder-diffraction experiments.^{13,15,18} However, resistivity²¹ and muon-spin relaxation²² studies indicate a low-temperature phase transition at 5–6 K. Our NdFeAsO single crystals show two low-temperature transitions in addition to the high-temperature transitions at $T_S \sim 142$ K and $T_N \sim 137$ K. Below $T^* \sim 15$ K, the Fe moments undergo a strongly hysteretic magnetic transition from AFM arrangement to a ferromagnetic (FM) arrangement along the *c* direction but unchanged AFM stripelike order in the (*ab*) plane. The Nd moments order AFM below $T_{Nd} \sim 6$ K, coupled to

the Fe magnetic order by a common magnetic unit cell, indicating a complex interplay between Nd and Fe magnetism.

NdFeAsO single crystals were grown out of NaAs flux as described in Ref. 20. Batches with millimeter-sized single crystals and masses up to 7 mg were carefully examined by wavelength dispersive spectroscopy (WDS) in a JEOL JXA-8200 Superprobe electron probe microanalyzer and x-ray powder diffraction. As in Ref. 20, WDS measurements on different samples from the same batch show no noticeable compositional variation and confirmed, within the limits of the measurement, the atomic ratio of 1:1:1:1. No impurity phases were detected beyond the NaAs flux.

Specific heat and resistivity were measured in a Quantum Design physical property measurement system²³ by the relaxation method and the four-probe technique using Epotek H20E silver epoxy contacts on platinum leads. The homogeneity of the batches was examined by resistivity measurements of several single crystals showing similar behavior. The reproducibility and excellent homogeneity of the grown material were additionally confirmed by neutron-diffraction measurements on polycrystalline samples consisting of more than 300 crystals. They showed well-defined transition temperatures and Bragg peaks in excellent agreement with the single-crystal measurements reported here. To check potential ferromagnetism, the magnetization, *M*, was measured with increasing temperature from 5 to 20 K for 11 fields, *H*, between 0.1 and 5 T and the differential susceptibility was calculated at each temperature. Parallel to the *c* axis, the zero-field intercept of the *M* vs *H* line characterizing a FM component was essentially temperature independent giving an upper limit of $0.012 \mu_B/f.u.$ Perpendicular to the *c* axis the value was an order of magnitude smaller.

The lattice distortion was characterized by high-resolution x-ray diffraction measurements using a four-circle diffractometer and Cu *K* α 1 radiation from a rotating anode x-ray source, selected by a Ge(1 1 1) monochromator. The plate-like single crystal was attached to a flat copper sample holder

on the cold finger of a closed-cycle dilplex refrigerator. A mosaicity of $\sim 0.03^\circ$ was determined from full width at half maximum of the rocking curve of the (0 0 6) Bragg peak. The orthorhombic distortion, δ , was determined as described in Ref. 24 using $(\xi \xi 0)$ scans through the tetragonal (1 1 7) Bragg peak which splits into the orthorhombic (2 0 7) and (0 2 7) Bragg peaks below T_S .

The neutron-diffraction experiments were carried out using the BT9 thermal-neutron triple-axis spectrometer at NCNR, NIST. The crystal with a mass of 3 mg was mounted on a thin aluminum post, oriented in the orthorhombic ($h 0 l$) scattering plane, and placed in an ILL cryostat. Rocking scans were resolution limited, indicating the high quality of the sample. Neutrons with a fixed incident energy of 14.7 meV and a collimation of $40' - 48' - \text{sample} - 40' - \text{open}$ were used. Additional measurements were taken on a number of crystals heat treated in various ways to check the results, and the observed transitions were all consistent within uncertainties. Descriptions are given in terms of the orthorhombic crystallographic (nuclear) unit cell present below T_S .

In Fig. 1, we compare the four measurements as a function of temperature. The anomaly at $T_S \sim 142$ K in specific-heat and resistivity measurements correlates with the phase transition from tetragonal $P4/nmm$ to orthorhombic $Cmma$. The orthorhombic lattice distortion, δ , increases below T_S for decreasing temperature without further anomalies. Figure 2(a) shows the splitting of the tetragonal (2 2 0) Bragg peak into the orthorhombic (4 0 0) and (0 4 0) Bragg peaks from our high-resolution neutron-diffraction measurements and demonstrates the bulk nature of the lattice distortion and the homogeneity of the sample, through resolution-limited peak shapes and a uniform transition temperature.

The second anomaly found in specific-heat and resistivity data at $T_N \sim 137$ K corresponds to the onset of the well-known AFM stripelike Fe order.¹² The intensity of the magnetic (1 0 3/2) Bragg peak increases smoothly below T_N [see Fig. 1(d)]. The inset illustrates that this transition shows no hysteresis upon cooling and warming through T_N consistent with a second-order transition.

At low temperature, a weak and broad anomaly in the resistivity can be associated with the disappearance of the magnetic (1 0 3/2) Bragg peak at $T^* \sim 15$ K signaling a change in the Fe magnetic order. This behavior is demonstrated in Fig. 2(c) by rocking scans through the (1 0 3/2) peak at selected temperatures. At the same temperature, T^* , new magnetic Bragg peaks occur as illustrated in Fig. 2(b) by the (1 0 1) peak and in Fig. 1(d) by the (1 0 0) peak. The intensity of these peaks increases with decreasing temperature as the Fe order changes while below $T_{Nd} \sim 6$ K the increase is much more pronounced. At T_{Nd} , a sharp peak is also observed in the specific heat [see inset of Fig. 1(a)] and the temperature derivative of the resistivity indicating the onset of the Nd magnetic order.

Details of the temperature dependence for these low-temperature transitions are shown in Fig. 3. The transition at $T^* \sim 15$ K shows hysteretic behavior illustrated in Fig. 3(b), through the temperature dependence of the magnetic (1 0 3/2) and (1 0 1) Bragg peaks. The strong hysteresis of approx. 3 K points to the first-order character of this transition at T^* . As illustrated in Fig. 3, the (1 0 0) and (1 0 1) Bragg

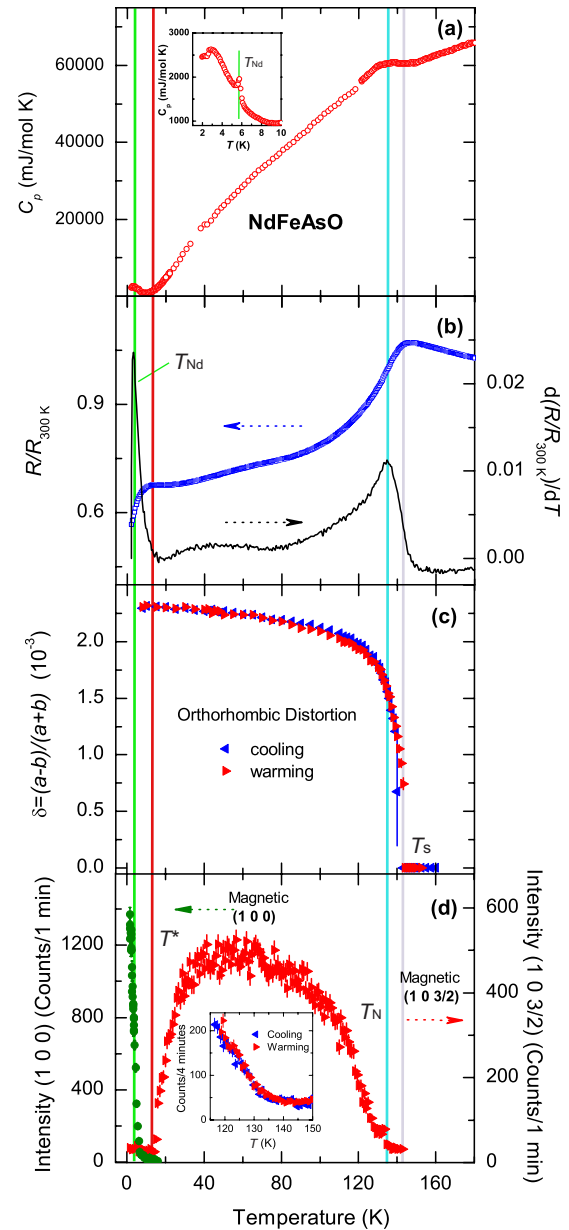


FIG. 1. (Color online) (a) Temperature dependence of the specific heat. (b) Resistivity (open symbol, left axis) and its derivative (line, right axis). (c) Orthorhombic distortion, δ , determined by x-ray diffraction as described in the text. (d) Neutron peak intensity for the magnetic Bragg peaks at (1 0 0) (left axis) and at (1 0 3/2) (right axis). The insets show expanded scales.

peaks follow the same trend with (i) weak intensity between T^* and T_{Nd} , and (ii) a strong but smooth and monotonic intensity increase below T_{Nd} without reaching saturation down to the lowest measured temperature of 1.5 K. Both low-temperature transitions are reminiscent of Nd_2CuO_4 , where the Nd-Cu coupling leads to abrupt changes in the Cu spin structure along with a significant induced Nd moment before the Nd spontaneously orders.^{25–27} It will be interesting to determine theoretically if a similar type of Fe-Nd coupling is the origin of this behavior in NdFeAsO.

For the determination of the magnetic structures, a series of five crystallographic and 7, 5, and 15 magnetic Bragg-

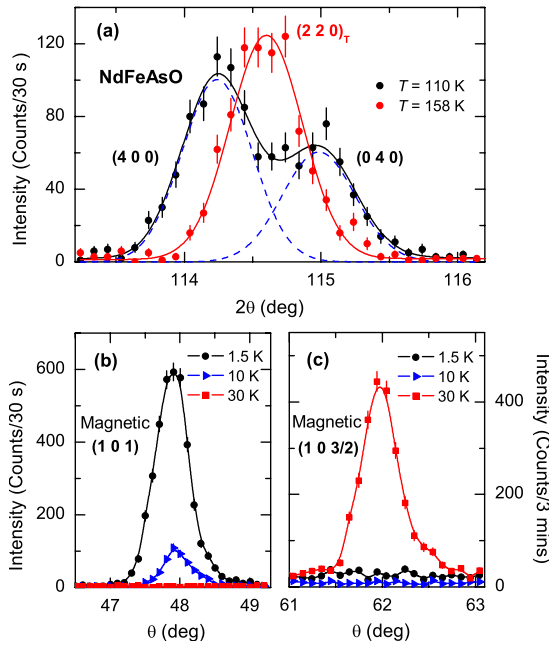


FIG. 2. (Color online) (a) Neutron-diffraction θ - 2θ scans through the tetragonal $(2\ 2\ 0)$ nuclear Bragg peak at $T=158$ K and its splitting into two orthorhombic Bragg peaks at $T=110$ K measured with reduced collimation of $10'-10'$ -sample- $10'-10'$. Neutron diffraction rocking scans through the magnetic Bragg peaks at (b) $(1\ 0\ 1)$ and (c) $(1\ 0\ 3/2)$ at selected temperatures.

peak intensities were measured by rocking scans at $T=30$ K, 10 K, and 1.5 K, respectively, and corrected for instrumental resolution. The crystallographic Bragg peaks were fit using the published crystal structure¹³ to determine the scale factor as the only refinable parameter. The value of the Fe magnetic moment was then determined from the intensity of the magnetic Bragg peaks considering equal domain averaging and using this scale factor and the magnetic structure models given below.

At $T^* < T < 30$ K $< T_N$ we find the same stripelike AFM structure previously reported.¹² The Fe moments are collinearly aligned along the a axis with AFM arrangement in the a and c directions and FM in the b direction. The magnetic unit cell for this magnetic structure is doubled along the c direction with respect to the orthorhombic crystallographic (nuclear) unit cell and yields the observed magnetic Bragg peaks at positions indexed by a propagation vector of $(1\ 0\ 1/2)$. The determined value of $0.54(3)\mu_B$ for the Fe moment is larger than the previously reported value of $0.25(7)\mu_B$.¹² The reason for this difference is unknown and points to differences between polycrystalline and single-crystal samples (potential small deviations in stoichiometry or strain). However, we note that the magnetic peaks associated with iron ordering were not reported in several other neutron powder scattering experiments.^{13,15,18}

The magnetic diffraction pattern at $T_{Nd} < T < 10$ K $< T^*$ can be indexed using a magnetic unit-cell identical to the orthorhombic crystallographic (nuclear) unit cell. In particular, no doubling along the c direction is now required, signaling a change from AFM ordering in this direction above T^* to FM ordering below T^* . Together with the unchanged

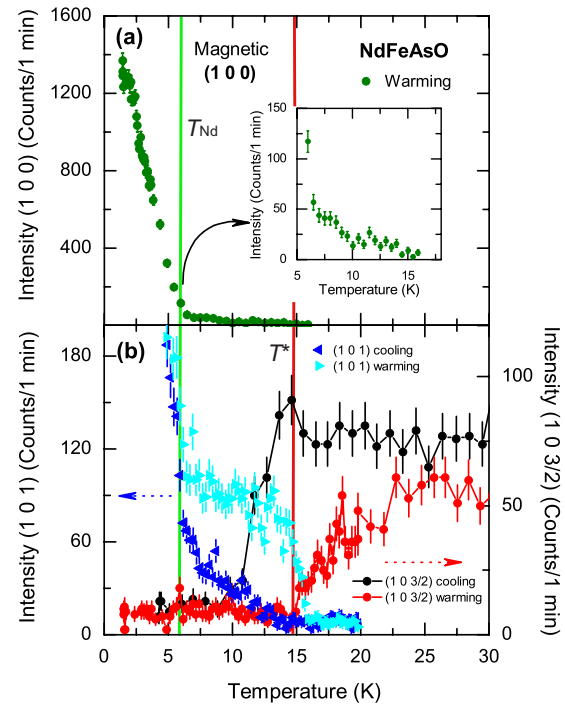


FIG. 3. (Color online) Neutron peak intensity for the magnetic Bragg peaks at (a) $(1\ 0\ 0)$ and (b) at $(1\ 0\ 1)$ (left axis) and $(1\ 0\ 3/2)$ (right axis). The inset in (a) shows an expanded scale between T_{Nd} and T^* .

stripelike order in the (ab) plane, this magnetic structure is simply described by a propagation vector of $(1\ 0\ 0)$. The intensity of all measured magnetic Bragg peaks can still be fit by Fe moments alone with a reduced moment value of $0.32(3)\mu_B$ collinearly aligned along the orthorhombic a axis.

At $T < T_{Nd}$, the strongly enhanced intensity of the magnetic Bragg peaks indicates the onset of the Nd magnetic order. The description of the magnetic diffraction pattern requires both Fe and Nd moments to be ordered. The positions of the magnetic Bragg peaks are consistent with the reported low-temperature magnetic structure.^{13,15} However, further measurements are necessary for a detailed analysis of the magnetic structure with its extensive number of parameters. The potential overlapping of Bragg peaks from twin domains with different orientations together with the small orthorhombicity require experiments with higher resolution or the usage of detwinned samples.

Summarizing, below $T_N \sim 137$ K, the Fe moments order AFM with the ubiquitous stripelike arrangement in the orthorhombic (ab) plane. For $T < T^* \sim 15$ K the c -axis configuration changes from AFM as observed in LaFeAsO (Ref. 2) to FM as found in CeFeAsO (Ref. 28) and PrFeAsO.^{29,30} This temperature-dependent change in the Fe magnetic order in NdFeAsO is unique in the RFeAsO series and demonstrates that the magnetic coupling in the c direction is at the border between AFM and FM. Further studies of RFeAsO compounds with other R elements are necessary to determine whether this delicate balance in the magnetic coupling is controlled by steric effects or the magnetocrystalline anisotropy of the R element caused by crystal-electric field effects

transferred through a complex coupling of the Nd and Fe magnetism. The proximity between the characteristic temperatures for the order-order transition of the Fe magnetic order at T^* to the onset of the Nd magnetic order at $T_{\text{Nd}} \sim 6$ K together with a common magnetic unit cell at low temperatures suggests the second case as the more likely scenario.

Research at Ames Laboratory and Oak Ridge National Laboratory was supported by the U.S. Department of Energy, Office of Basic Energy Science, Division of Materials Sciences and Engineering and Scientific User Facilities Division, respectively. Ames Laboratory is operated for the U.S. Department of Energy by Iowa State University under Contract No. DE-AC02-07CH11358.

- ¹Y. Kamihara, T. Watanabe, M. Hirano, and H. Hosono, *J. Am. Chem. Soc.* **130**, 3296 (2008).
- ²C. de la Cruz, Q. Huang, J. W. Lynn, J. Li, W. Ratcliff II, J. L. Zarestky, H. A. Mook, G. F. Chen, J. L. Luo, N. L. Wang, and P. Dai, *Nature (London)* **453**, 899 (2008).
- ³A. S. Sefat, M. A. McGuire, B. C. Sales, R. Jin, J. Y. Howe, and D. Mandrus, *Phys. Rev. B* **77**, 174503 (2008).
- ⁴Z. A. Ren, J. Yang, W. Lu, W. Yi, G. C. Che, X. L. Dong, L. Sun, and Z. Zhao, *Mater. Res. Innovations* **12**, 105 (2008).
- ⁵Z.-A. Ren, J. Yang, W. Lu, W. Yi, X.-L. Shen, Z.-C. Li, G.-C. Che, X.-L. Dong, L.-L. Sun, F. Zhou, and Z.-X. Zhao, *EPL* **82**, 57002 (2008).
- ⁶G. F. Chen, Z. Li, D. Wu, G. Li, W. Z. Hu, J. Dong, P. Zheng, J. L. Luo, and N. L. Wang, *Phys. Rev. Lett.* **100**, 247002 (2008).
- ⁷Z.-A. Ren, G.-C. Che, X.-L. Dong, J. Yang, W. Lu, W. Yi, X.-L. Shen, Z.-C. Li, L.-L. Sun, F. Zhou, and Z.-X. Zhao, *EPL* **83**, 17002 (2008).
- ⁸J. Yang, Z.-C. Li, W. Lu, W. Yi, X.-L. Shen, Z.-A. Ren, G.-C. Che, X.-L. Dong, L.-L. Sun, F. Zhou, and Z.-X. Zhao, *Supercond. Sci. Technol.* **21**, 082001 (2008).
- ⁹J. W. G. Bos, G. B. S. Penny, J. A. Rodgers, D. A. Sokolov, A. D. Huxley, and J. P. Attfield, *Chem. Commun. (Cambridge)* **2008**, 3634.
- ¹⁰R. H. Liu, G. Wu, T. Wu, D. F. Fang, H. Chen, S. Y. Li, K. Liu, Y. L. Xie, X. F. Wang, R. L. Yang, L. Ding, C. He, D. L. Feng, and X. H. Chen, *Phys. Rev. Lett.* **101**, 087001 (2008).
- ¹¹C. Wang, L. Li, S. Chi, Z. Zhu, Z. Ren, Y. Li, Y. Wang, X. Lin, Y. Luo, S. Jiang, X. Xu, G. Cao, and Z. Xu, *EPL* **83**, 67006 (2008).
- ¹²Y. Chen, J. W. Lynn, J. Li, G. Li, G. F. Chen, J. L. Luo, N. L. Wang, P. Dai, C. de la Cruz, and H. A. Mook, *Phys. Rev. B* **78**, 064515 (2008).
- ¹³Y. Qiu, W. Bao, Q. Huang, T. Yildirim, J. M. Simmons, M. A. Green, J. W. Lynn, Y. C. Gasparovic, J. Li, T. Wu, G. Wu, and X. H. Chen, *Phys. Rev. Lett.* **101**, 257002 (2008).
- ¹⁴Q. Huang, J. Zhao, J. W. Lynn, G. F. Chen, J. L. Luo, N. L. Wang, and P. Dai, *Phys. Rev. B* **78**, 054529 (2008).
- ¹⁵A. Marcinkova, E. Suard, A. N. Fitch, S. Margadonna, and J. W. G. Bos, *Chem. Mater.* **21**, 2967 (2009).
- ¹⁶D. H. Ryan, J. M. Cadogan, C. Ritter, F. Canepa, A. Palenzona, and M. Putti, *Phys. Rev. B* **80**, 220503(R) (2009).
- ¹⁷A. Marcinkova, D. A. M. Grist, I. Margiolaki, T. C. Hansen, S. Margadonna, and Jan-Willem G. Bos, *Phys. Rev. B* **81**, 064511 (2010).
- ¹⁸L. Malavasi, G. A. Artioli, C. Ritter, M. C. Mozzati, B. Maroni, B. Pahari, and A. Caneschi, *J. Am. Chem. Soc.* **132**, 2417 (2010).
- ¹⁹A. D. Christianson, E. A. Goremychkin, R. Osborn, S. Rosenkranz, M. D. Lumsden, C. D. Malliakas, I. S. Todorov, H. Claus, D. Y. Chung, M. G. Kanatzidis, R. I. Bewley, and T. Guidi, *Nature (London)* **456**, 930 (2008).
- ²⁰J.-Q. Yan, S. Nandi, J. L. Zarestky, W. Tian, A. Kreyssig, B. Jensen, A. Kracher, K. W. Dennis, R. J. McQueeney, A. I. Goldman, R. W. McCallum, and T. A. Lograsso, *Appl. Phys. Lett.* **95**, 222504 (2009).
- ²¹P. Cheng, H. Yang, Y. Jia, L. Fang, X. Zhu, G. Mu, and H.-H. Wen, *Phys. Rev. B* **78**, 134508 (2008).
- ²²A. A. Aczel, E. Baggio-Saitovitch, S. L. Bud'ko, P. C. Canfield, J. P. Carlo, G. F. Chen, P. Dai, T. Goko, W. Z. Hu, G. M. Luke, J. L. Luo, N. Ni, D. R. Sanchez-Candela, F. F. Tafti, N. L. Wang, T. J. Williams, W. Yu, and Y. J. Uemura, *Phys. Rev. B* **78**, 214503 (2008).
- ²³Any mention of commercial products within this Rapid Communication is for information only; it does not imply recommendation or endorsement by NIST.
- ²⁴S. Nandi, M. G. Kim, A. Kreyssig, R. M. Fernandes, D. K. Pratt, A. Thaler, N. Ni, S. L. Bud'ko, P. C. Canfield, J. Schmalian, R. J. McQueeney, and A. I. Goldman, *Phys. Rev. Lett.* **104**, 057006 (2010).
- ²⁵S. Skanthakumar, H. Zhang, T. W. Clinton, W.-H. Li, J. W. Lynn, Z. Fisk, and S.-W. Cheong, *Physica C* **160**, 124 (1989).
- ²⁶J. W. Lynn, I. W. Sumarlin, S. Skanthakumar, W.-H. Li, R. N. Shelton, J. L. Peng, Z. Fisk, and S.-W. Cheong, *Phys. Rev. B* **41**, 2569 (1990).
- ²⁷R. Sachidanandam, T. Yildirim, A. B. Harris, A. Aharony, and O. Entin-Wohlman, *Phys. Rev. B* **56**, 260 (1997).
- ²⁸J. Zhao, Q. Huang, C. de la Cruz, S. Li, J. W. Lynn, Y. Chen, M. A. Green, G. F. Chen, G. Li, Z. Li, J. L. Luo, N. L. Wang, and P. Dai, *Nature Mater.* **7**, 953 (2008).
- ²⁹J. Zhao, Q. Huang, C. de la Cruz, J. W. Lynn, M. D. Lumsden, Z. A. Ren, J. Yang, X. Shen, X. Dong, Z. Zhao, and P. Dai, *Phys. Rev. B* **78**, 132504 (2008).
- ³⁰S. A. J. Kimber, D. N. Argyriou, F. Yokaichiya, K. Habicht, S. Gerischer, T. Hansen, T. Chatterji, R. Klingeler, C. Hess, G. Behr, A. Kondrat, and B. Büchner, *Phys. Rev. B* **78**, 140503(R) (2008).