

2-1-2016

Nonmonotonic pressure evolution of the upper critical field in superconducting FeSe

Udhara S. Kaluarachchi
Iowa State University and Ames Laboratory

Valentin Taufour
Ames Laboratory

Anna E. Böhrmer
Ames Laboratory

Makariy A. Tanatar
Iowa State University and Ames Laboratory, tanatar@ameslab.gov

Sergey L. Bud'ko
Iowa State University and Ames Laboratory, budko@ameslab.gov

See next page for additional authors

Follow this and additional works at: https://lib.dr.iastate.edu/physastro_pubs



Part of the [Condensed Matter Physics Commons](#)

The complete bibliographic information for this item can be found at https://lib.dr.iastate.edu/physastro_pubs/577.
For information on how to cite this item, please visit <http://lib.dr.iastate.edu/howtocite.html>.

This Article is brought to you for free and open access by the Physics and Astronomy at Iowa State University Digital Repository. It has been accepted for inclusion in Physics and Astronomy Publications by an authorized administrator of Iowa State University Digital Repository. For more information, please contact digirep@iastate.edu.

Nonmonotonic pressure evolution of the upper critical field in superconducting FeSe

Abstract

The pressure dependence of the upper critical field, $H_{c2,c}$, of single crystalline FeSe was studied using measurements of the interplane resistivity, ρ_c , in magnetic fields parallel to tetragonal c axis. $H_{c2,c}(T)$ curves obtained under hydrostatic pressures up to 1.56 GPa, the range over which the superconducting transition temperature, T_c , of FeSe exhibits a nonmonotonic dependence with local maximum at $p_1 \approx 0.8$ GPa and local minimum at $p_2 \approx 1.2$ GPa. The slope of the upper critical field at T_c , $(dH_{c2,c}/dT)_{T_c}$, also exhibits a nonmonotonic pressure dependence with distinct changes at p_1 and p_2 . For $p > p_2$ the slope is in good *semiquantitative* agreement with a single band, orbital Helfand-Werthamer theory with Fermi velocities determined from Shubnikov–de Haas measurements. This finding indicates that Fermi surface changes are responsible for the local minimum of $T_c(p)$ at $p_2 \approx 1.2$ GPa.

Disciplines

Condensed Matter Physics

Comments

This article is published as Kaluarachchi, Udhara S., Valentin Taufour, Anna E. Böhmer, Makariy A. Tanatar, Sergey L. Bud'ko, Vladimir G. Kogan, Ruslan Prozorov, and Paul C. Canfield. "Nonmonotonic pressure evolution of the upper critical field in superconducting FeSe." *Physical Review B* 93, no. 6 (2016): 064503. DOI: [10.1103/PhysRevB.93.064503](https://doi.org/10.1103/PhysRevB.93.064503). Posted with permission.

Authors

Udhara S. Kaluarachchi, Valentin Taufour, Anna E. Böhmer, Makariy A. Tanatar, Sergey L. Bud'ko, Vladimir G. Kogan, Ruslan Prozorov, and Paul C. Canfield

Nonmonotonic pressure evolution of the upper critical field in superconducting FeSeUdhara S. Kaluarachchi,^{1,2} Valentin Taufour,¹ Anna E. Böhmer,¹ Makariy A. Tanatar,^{1,2} Sergey L. Bud'ko,^{1,2}
Vladimir G. Kogan,¹ Ruslan Prozorov,^{1,2} and Paul C. Canfield^{1,2}¹*Ames Laboratory U.S. DOE, Iowa State University, Ames, Iowa 50011, USA*²*Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA*

(Received 27 November 2015; revised manuscript received 8 January 2016; published 1 February 2016)

The pressure dependence of the upper critical field, $H_{c2,c}$, of single crystalline FeSe was studied using measurements of the interplane resistivity, ρ_c , in magnetic fields parallel to tetragonal c axis. $H_{c2,c}(T)$ curves obtained under hydrostatic pressures up to 1.56 GPa, the range over which the superconducting transition temperature, T_c , of FeSe exhibits a nonmonotonic dependence with local maximum at $p_1 \approx 0.8$ GPa and local minimum at $p_2 \approx 1.2$ GPa. The slope of the upper critical field at T_c , $(dH_{c2,c}/dT)_{T_c}$, also exhibits a nonmonotonic pressure dependence with distinct changes at p_1 and p_2 . For $p < p_1$ the slope can be described within a multiband orbital model. For both $p_1 < p < p_2$ and $p > p_2$ the slope is in good *semiquantitative* agreement with a single band, orbital Helfand-Werthamer theory with Fermi velocities determined from Shubnikov-de Haas measurements. This finding indicates that Fermi surface changes are responsible for the local minimum of $T_c(p)$ at $p_2 \approx 1.2$ GPa.

DOI: [10.1103/PhysRevB.93.064503](https://doi.org/10.1103/PhysRevB.93.064503)**I. INTRODUCTION**

Hydrostatic pressure is a widely used tool to study materials without changing their stoichiometry. Pressure is a particularly useful, nonthermal tuning parameter for quantum critical materials, in which suppression of antiferromagnetic ordering temperature T_N to zero at a quantum critical point [1] leads to strong deviations of electronic properties from standard Fermi-liquid theory and superconductivity. Iron-based superconductors provide one of the most clear examples of quantum critical systems [2], with T -linear resistivity [3,4] and maximum T_c at optimal doping found at the edge of magnetic ordering in x or pressure p . However, notable deviations from this simple picture are found in K- and Na-hole-doped BaFe_2As_2 -based compositions (BaK122 and BaNa122 in the following). Here suppression of $T_N(x)$ to zero happens at significantly lower x than maximum T_c is achieved [5–8], and, moreover, T_c reveals a nonmonotonic composition dependence near $x \approx 0.25$ [9,10], and pressure dependence for close compositions [11–13], reminiscent of the 1/8 anomaly in the underdoped cuprates [14]. This $x = 0.25$ anomaly in $T_c(x, p)$ was related with the emergence of competing magnetic phase [10].

FeSe is structurally the simplest iron-based superconductor [15–17], but it has one of the more complex pressure-temperature phase diagrams. At ambient pressure FeSe undergoes electronic nematic tetragonal to orthorhombic structural transition with $T_s \approx 90$ K, which is not accompanied by long-range magnetic ordering [18], and becomes superconducting with $T_c \approx 8.5$ K [19]. The application of quasihydrostatic pressure leads to a fourfold increase of T_c up to 37 K [20], and the rise of T_c continues well beyond the point where $T_s(p) \rightarrow 0$ at $p \sim 2$ GPa. Even much higher T_c values up to ~ 100 K are claimed in single layer films of FeSe [21]. Interestingly, the increase of T_c with pressure in bulk FeSe is not monotonic: $T_c(p)$ shows a local maximum at $p_1 \approx 0.8$ GPa, a local minimum at $p_2 \approx 1.2$ GPa, before rising monotonically with further pressure increase up to ≈ 8 GPa. The origin of this nonmonotonic pressure evolution of T_c in FeSe is a subject of

intense studies. The local maximum of T_c was related with the emergence of a competing phase [22], presumably of magnetic origin as observed in μSR and NMR studies [23–25]. The minimum at p_2 (strongly resembling pressure anomaly in the underdoped BaK122 [11]) can be merely a restoration of a rise of T_c with pressure after a decrease at p_1 , or represent a modification of the superconducting gap structure.

A nonmonotonic variation of T_c under pressure was also observed in KFe_2As_2 [26–28]. Taufour *et al.* [28] used measurements of the upper critical field to gain insight into the origin of this anomaly and suggested modification of the superconducting gap structure. Considering the complex evolution of the superconducting transition temperature with pressure in FeSe, measurements of H_{c2} can shed light on the pressure evolution of the superconducting state of this material.

In this paper we report the study of the pressure evolution of the orbital upper critical field $H_{c2,c}$ as a probe of superconductivity in FeSe. We use interplane resistivity measurements in longitudinal configuration with parallel current and magnetic field, $H \parallel j \parallel c$ to minimize the contribution of flux flow phenomena and obtain sharp superconducting transitions. We find a semiquantitative agreement for the experimental slope, $(dH_{c2,c}/dT)_{T_c}$, evaluated at the superconducting transition temperature T_c and single - band Helfand-Werthamer [29] calculations using Fermi velocities determined from recent Shubnikov-de Haas (SdH) oscillations [30] for $p > p_1$, and even rough agreement in the multiband case for $p < p_1$. Three pressure ranges with the characteristic behavior of $T_c(p)$ can be linked with the changes of $H_{c2,c}$ and of the Fermi surface.

II. EXPERIMENTAL METHODS

Single crystals of FeSe were grown using a modified chemical vapor transport technique [31]. The c -axis resistivity of FeSe was measured using a two-probe technique [32,33] relying on negligible contact resistance. Two Ag wires (50 μm diameter) were attached to the samples by soldering with In-Ag alloy, giving contacts with resistance less than 10 $\mu\Omega$. Four-probe measurements were used down to the sample contacts,

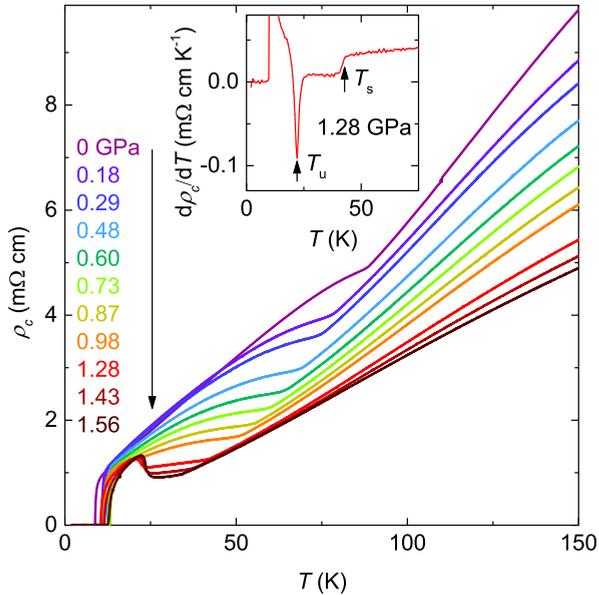


FIG. 1. Evolution of the temperature dependence of the c -axis resistivity, ρ_c , with hydrostatic pressure. The inset presents the derivative of $\rho_c(T)$ taken at 1.28 GPa, with arrows indicating the temperatures of the structural transition, T_s , and of the “unknown” transition, T_u , which is presumably associated with magnetic ordering.

so that the measured resistance represents the sum of series connected sample and contact resistances, $R_{\text{sample}} + R_{\text{contact}}$. Because $R_{\text{contact}} \ll R_{\text{sample}}$, the contact resistance gives minor correction, of the order of 1%, to measured quantity. This can be directly seen from the negligible measured resistance at temperatures below superconducting transition of FeSe (see Fig. 1 below). Measurements were performed in a Quantum Design PPMS, on cooling and warming at a rate 0.25 K/min. We used a Be-Cu/Ni-Cr-Al hybrid piston-cylinder cell, similar to the one described in Ref. [34]. Pressure values at low temperatures were inferred from $T_c(p)$ of lead [35]. Good hydrostatic pressure conditions, as seen by sharp superconducting transitions of both the sample and Pb resistive manometer, were achieved by using a pressure medium of 4:6 mixture of light mineral oil : n -pentane [34,36] that solidifies at room temperature at ~ 3 –4 GPa, well above our maximum pressure. The orientation of the sample in the pressure cell was adjusted so that the magnetic field was applied parallel to the c -axis direction.

III. RESULTS AND DISCUSSION

Figure 1 shows the temperature dependence of the c -axis resistivity, ρ_c , taken at various pressures. At ambient pressure the interplane resistivity decreases on cooling and shows an anomaly associated with the structural phase transition at $T_s \sim 86$ K and a sharp superconducting transition at $T_c \sim 9.5$ K. The residual resistivity ratio values are found to be 17 for the c -axis data shown in this work and 22 for ab -plane data shown in Ref. [37]. Similar values of T_s and T_c have been obtained in previous in-plane resistivity (ρ_{ab}) studies [20,22,38]. Note, however, that the anomaly at T_s is much more prominent in $\rho_c(T)$. With

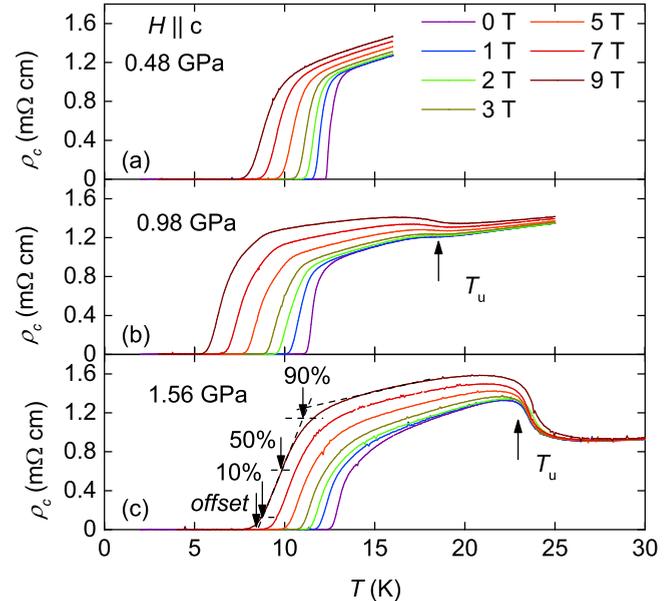


FIG. 2. Temperature dependence of the interplane resistivity, $\rho_c(T)$, taken in magnetic fields of the 0–9 T range in the $H \parallel c$ configuration at pressures of 0.48 GPa (a), 0.98 GPa (b), and 1.56 GPa (c). The upper critical field $H_{c2,c}$ is determined from the offset, 10%, 50%, and 90% of ρ_c as shown schematically by the arrows in the bottom panel for the 9 T curve and unless otherwise stated, the offset criterion is used in this paper. The temperature of the unknown transition, T_u , manifests a very weak dependence on external magnetic fields up to 9 T.

increasing pressure, the resistivity at 150 K monotonically decreases and T_s is also suppressed. A sudden increase of ρ_c on cooling below $T_u \sim 15$ K, as seen for pressure above 0.87 GPa, marks the emergence of a new, most likely magnetically ordered [22–24], phase. The pressure range of this phase in our experiments is consistent with the previous report of Ref. [22] (see below). Note that the anomaly at T_u is also more prominent in $\rho_c(T)$ than in ρ_{ab} . No measurable temperature hysteresis is found for any of the transitions. The values of T_s and T_u were obtained from the features in the resistivity derivative (inset of Fig. 1). They were tracked as functions of applied pressure to determine the p - T phase diagram of the compound, as shown in Fig. 4 below.

Figure 2 shows the evolution of the interplane resistivity, $\rho_c(T)$, in the vicinity of the superconducting transition with magnetic fields of the 0–9 T range. The data are shown for representative pressures of 0.48 GPa (a), 0.98 GPa (b), and 1.56 GPa (c). T_c was defined using an offset criterion as schematically shown in Fig. 2(c) for the 9 T curve. At ambient pressure the superconducting transition remains quite sharp for all field values. The transition broadens slightly at higher pressures and magnetic fields. Whereas the T_c is suppressed at a similar rate at 0.48 and 1.56 GPa [Figs. 2(a) and 2(c)], it is suppressed much faster at the intermediate pressure range at 0.98 GPa [Fig. 2(b)]. We note that T_u only shows a weak dependence on an applied magnetic field up to 9 T [see Figs. 2(b) and 2(c)].

The pressure evolution of the temperature-dependent upper critical field $\mu_0 H_{c2,c}$, measured in $H \parallel c$ configuration, is

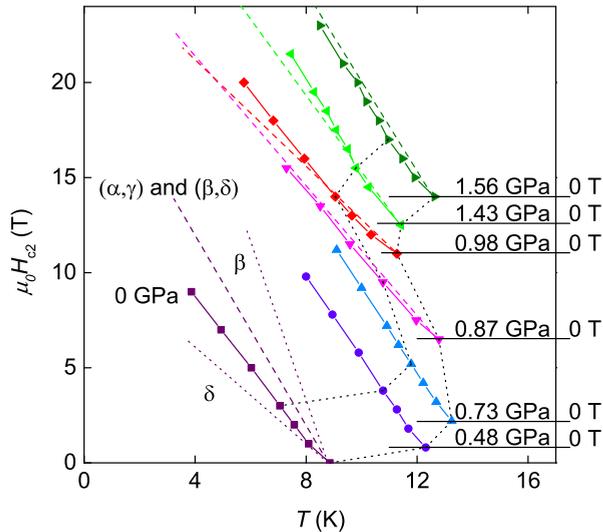


FIG. 3. The temperature dependence of the upper critical field $H_{c2,c}(T)$ measured in $H \parallel c$ configuration under various pressures. The data are vertically offset to avoid overlapping, with horizontal lines showing $H = 0$. Dashed lines represent upper critical field slopes calculated based on the Fermi velocity, v_F , from Ref. [30] for a cylindrical Fermi surface [39] (see text). At 0 GPa, two dotted and dashed lines represent calculated slopes for the largest (δ), smallest (β), and average v_F [(α, γ) and (β, δ)]. Black dotted lines connect the 0 and 3 T points for various pressures.

summarized in Fig. 3. The symbols connected by solid lines represent the experimental data, the curves for different pressures are offset to avoid overlapping, and $H = 0$ origin for each pressure is shown by solid horizontal lines. We can clearly see that the slope of $H_{c2,c}$ at T_c , $dH_{c2,c}/dT|_{T_c}$, is fairly constant between 0 and 0.73 GPa, decreases markedly when the pressure is increased to 0.87 GPa, and increases again at 1.43 GPa.

Generally, the upper critical field is determined by the orbital and Pauli pair breaking effects. Near T_c , the Pauli limit is irrelevant and the slope, $dH_{c2,c}/dT|_{T_c}$, can be estimated in the clean limit for cylindrical Fermi surfaces as [39]

$$-\mu_0 \frac{dH_{c2}}{dT} \Big|_{T_c} = \frac{16\pi k_B^2 \Phi_0 T_c}{7\zeta(3)\hbar^2(n_1\lambda_{11}\langle v_1^2 \rangle + n_2\lambda_{22}\langle v_2^2 \rangle)}, \quad (1)$$

where $n_1 = N_1/N_{\text{total}}$ and $n_2 = N_2/N_{\text{total}}$ are the partial densities of states which can be obtained from $N_i \propto m_i^* k_{F,i}$. v_i are the Fermi velocity, m_i^* the effective mass, and $k_{F,i}$ the Fermi wave vector of the respective band $i = (1, 2)$. λ_{11} and the λ_{22} are the normalized coupling constant [39] and Φ_0 is the flux quantum.

To compare the pressure evolution of the upper critical field with changes of the Fermi surface, we calculate the $dH_{c2,c}/dT|_{T_c}$ with Eq. (1), using v_F values determined in recent quantum oscillation studies by Terashima *et al.* [30]. The calculated $dH_{c2,c}/dT|_{T_c}$ represented by the dashed lines in Fig. 3 shows semiquantitative agreement with the experimental slopes. This agreement is good particularly for pressures above 0.6 GPa, where only one fundamental frequency is observed in SdH studies. This allows us to select $n_1 = \lambda_{11} = 1$ and $n_2 = \lambda_{22} = 0$ in Eq. (1). The calculated slopes

reproduce very well the experimental data up to the highest pressure 1.56 GPa of our experiment, including the increase of the slope between 0.98 and 1.43 GPa. The situation is more complicated for pressures below 0.6 GPa, where four fundamental frequencies, α , β , γ , and δ are observed in SdH measurements. As explained in Ref. [40], α and γ orbits are attributed to the electronlike Fermi pockets, whereas β and δ to the hole pockets. Following this assignment, we can calculate the average v_F and partial densities of states for each Fermi surface. We consider this system an effective two-band case and assume $\lambda_{11} = \lambda_{22}$ to estimate $dH_{c2,c}/dT|_{T_c}$ at zero pressure using Eq. (1). The result is shown by a dashed line in Fig. 3. For reference we also show the estimated slopes using extreme Fermi velocities: the largest, δ frequency, and the smallest, β frequency, as represented by the dotted lines. Hence the calculation reproduces the range of value for the slope. We point out that slight variation of the coupling constants can improve the match. This comparison suggests that the pressure evolution of the upper critical field over the whole range can be explained by measured Fermi velocities.

This finding contrasts with KFe_2As_2 , where a change in $(dH_{c2,c}/dT)/T_c$ as a function of pressure was measured, but could not be attributed to changes of the Fermi velocities [28]. Whereas this was taken as an indication for a change of the order parameter with pressure in KFe_2As_2 , the case of FeSe seems to be more conventional, as the changes in the upper critical field can be well explained by the observed change of Fermi velocities.

Figure 4 shows the pressure evolution of the slope $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ determined by a linear fit to $H_{c2,c}$ data in the field interval 0–3 T, and its relation to the temperature-pressure phase diagram of FeSe . The phase diagram [Fig. 4(a)] as determined from our interplane resistivity measurements is in perfect agreement with previous results determined from in-plane resistivity measurements [22,30,38]. The temperature of the nematic transition T_s shows a linear decrease with a slope of $dT_s/dp \approx -34$ K/GPa. The superconducting $T_c(p)$ has maximum and minimum around $p_1 \approx 0.8$ GPa and $p_2 \approx 1.2$ GPa, respectively. The maximum is located close to the point where anomaly at T_u emerges, likely signaling a magnetic phase transition [23–25]. Competition between superconductivity and magnetic order may be the reason for the suppression of T_c between p_1 and p_2 . In contrast, no anomalies which would correlate with either the maximum or the minimum of T_c are observed in T_s .

The existence of a maximum and a minimum in $T_c(p)$ makes us divide the phase diagram into three different regions: $p \lesssim p_1$ ($dT_c/dp > 0$), $p_1 \lesssim p \lesssim p_2$ ($dT_c/dp < 0$), and $p_2 \lesssim p$ ($dT_c/dp > 0$), as represented by the vertical dotted lines in Fig. 4. Interestingly, the pressure evolution of the normalized slope $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ [Fig. 4(b)] shows much more pronounced changes between the three ranges. In order to demonstrate that our results are not criteria dependent (see Fig. 2), Fig. 4(c) shows a comparison of the pressure dependence of $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ for the following criteria: offset, 10%, 50%, and 90% of the resistivity. Due to the curvature at the onset of the resistivity data, 90% criterion shows considerably higher $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ values than other criteria. However, we can clearly see that the overall

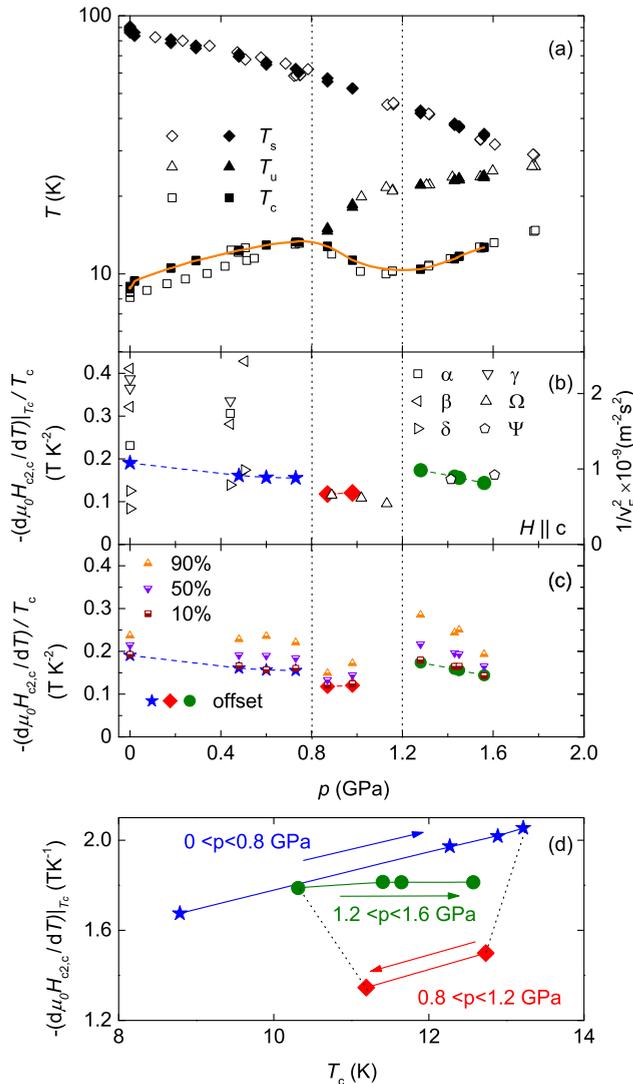


FIG. 4. (a) Temperature - pressure phase diagram of FeSe as determined from inter-plane resistivity measurements (full symbols) and from previous in-plane resistivity measurements (open symbols) [22,30,38]. The circles, triangles and squares represent the tetragonal/orthorhombic, unknown, most likely magnetic and superconducting phase transitions, respectively. The orange solid line is a guide for the eye. Vertical dotted lines show the pressures corresponding to the local maxima and minima of $T_c(p)$. (b) Pressure dependence of the normalized slope $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$. An abrupt change of slope is observed near 0.8 GPa and 1.2 GPa, corresponding to the maximum and a minimum in $T_c(p)$ (left axis). For reference we show v_F^{-2} calculated for individual orbits in Shubnikov-deHaas effect measurements of Ref. [30] (right axis). There is clear proportionality between the normalized slope and v_F^{-2} as found in our data analysis for $p > p_1$, despite both slope and v_F showing nonmonotonic changes at p_2 . Multiple orbits found for $p < p_1$ clearly illustrate the difficulty of $H_{c2,c}$ slope calculation in any simple model. (c) Pressure dependence of the normalized slope $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ for four different criteria; offset, 10%, 50% and 90% of the resistivity. (d) The slope of the $H_{c2,c}$ line plotted vs T_c with pressure as an implicit parameter. The plot clearly reveals the nonmonotonic dependence with three ranges separated at pressures p_1 and p_2 . Arrows indicate the direction of pressure increase.

behavior of pressure dependence of $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ does not depend on the chosen criteria.

The differences between the three pressure ranges are particularly visible when plotting the data as a function of T_c [Fig. 4(d)] with pressure as an implicit hidden parameter. In the low pressure range, $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ remains rather constant, then shows a sudden drop at $p_1 \approx 0.8$ GPa, where T_c has a maximum, and an increment around $p_2 \approx 1.2$ GPa where T_c reaches a local minimum [Fig. 4(b)]. Note that in the case of KFe_2As_2 , the abrupt change of the slope $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ also coincides with a minimum in $T_c(p)$ [28].

Simplifying Eq. (1) for the single-band case, one can relate the initial $H_{c2,c}$ slope to the Fermi velocity, v_F , and the effective mass, m^* , as $(-1/T_c)(dH_{c2,c}/dT)|_{T_c} \propto v_F^{-2} \propto (m^*)^2$. This dependence allows for a direct comparison between the initial slope of $H_{c2,c}$ and Fermiology. In Fig. 4(b) we plot the normalized slope of $H_{c2,c}$ (left axis) and v_F^{-2} (right axis). The two quantities show very similar pressure dependence, directly illustrating the validity of our previous analysis. This plot also provides a graphical illustration for the difficulty of quantitative comparison of the slope with Fermiology in the multiband case in particular, considering the possibility of variation of coupling constants.

The pressure evolution of $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ hence indicates a decrease of the effective masses with pressure in the low pressure range, a further sudden decrement around p_1 , and an increase of the effective mass around p_2 . This is indeed in good agreement with the quantum oscillation study [30]. It is notable, however, that $T_c(p)$ shows only smooth changes around these pressure values.

IV. CONCLUSIONS

In conclusion, the pressure evolution of the upper critical field of FeSe is in good agreement with the Fermi velocities determined from quantum oscillations. Abrupt changes in the normalized slope of the upper critical field $(-1/T_c)(dH_{c2,c}/dT)|_{T_c}$ of FeSe provide evidence for changes of the Fermi surface around 0.8 and 1.2 GPa, which correspond to the local maximum and minimum of T_c , respectively. We cannot exclude possible effects on change of order parameter and/or variation of the coupling under pressure may be the reason for the observed change in T_c . However, our study demonstrates that, in contrast to KFe_2As_2 , the nonmonotonic pressure evolution of T_c of FeSe can be fully accounted for by changes in the Fermi surface.

ACKNOWLEDGMENTS

We would like to thank A. Kreyssig and T. Kong for useful discussions and T. Terashima for sharing his quantum oscillation data for the comparison in this study. This work was carried out at the Iowa State University and supported by the Ames Laboratory, U.S. DOE, under Contract No. DE-AC02-07CH11358. V.T. is partially supported by Critical Material Institute, an Energy Innovation Hub funded by U.S. DOE, Office of Energy Efficiency and Renewal Energy, Advanced Manufacturing Office.

- [1] N. D. Mathur, F. M. Grosche, S. R. Julian, I. R. Walker, D. M. Freye, R. K. W. Haselwimmer, and G. G. Lonzarich, *Nature (London)* **394**, 39 (1998).
- [2] Y. Nakai, T. Iye, S. Kitagawa, K. Ishida, H. Ikeda, S. Kasahara, H. Shishido, T. Shibauchi, Y. Matsuda, and T. Terashima, *Phys. Rev. Lett.* **105**, 107003 (2010).
- [3] S. Kasahara, T. Shibauchi, K. Hashimoto, K. Ikada, S. Tonegawa, R. Okazaki, H. Shishido, H. Ikeda, H. Takeya, K. Hirata, T. Terashima, and Y. Matsuda, *Phys. Rev. B* **81**, 184519 (2010).
- [4] N. Doiron-Leyraud, P. Auban-Senzier, S. René de Cotret, C. Bourbonnais, D. Jérôme, K. Bechgaard, and L. Taillefer, *Phys. Rev. B* **80**, 214531 (2009).
- [5] M. Rotter, M. Tegel, and D. Johrendt, *Phys. Rev. Lett.* **101**, 107006 (2008).
- [6] S. Avci, O. Chmaissem, E. A. Goremychkin, S. Rosenkranz, J.-P. Castellán, D. Y. Chung, I. S. Todorov, J. A. Schlueter, H. Claus, M. G. Kanatzidis, A. Daoud-Aladine, D. Khalyavin, and R. Osborn, *Phys. Rev. B* **83**, 172503 (2011).
- [7] S. Avci, O. Chmaissem, D. Y. Chung, S. Rosenkranz, E. A. Goremychkin, J. P. Castellán, I. S. Todorov, J. A. Schlueter, H. Claus, A. Daoud-Aladine, D. D. Khalyavin, M. G. Kanatzidis, and R. Osborn, *Phys. Rev. B* **85**, 184507 (2012).
- [8] M. A. Tanatar, W. E. Straszheim, H. Kim, J. Murphy, N. Spyrison, E. C. Blomberg, K. Cho, J.-P. Reid, B. Shen, L. Taillefer, H.-H. Wen, and R. Prozorov, *Phys. Rev. B* **89**, 144514 (2014).
- [9] A. E. Böhmer, P. Burger, F. Hardy, T. Wolf, P. Schweiss, R. Fromknecht, M. Reinecker, W. Schranz, and C. Meingast, *Phys. Rev. Lett.* **112**, 047001 (2014).
- [10] J. M. Allred, S. Avci, D. Y. Chung, H. Claus, D. D. Khalyavin, P. Manuel, K. M. Taddei, M. G. Kanatzidis, S. Rosenkranz, R. Osborn, and O. Chmaissem, *Phys. Rev. B* **92**, 094515 (2015).
- [11] E. Hassinger, G. Gredat, F. Valade, S. R. de Cotret, A. Juneau-Fecteau, J.-P. Reid, H. Kim, M. A. Tanatar, R. Prozorov, B. Shen, H.-H. Wen, N. Doiron-Leyraud, and L. Taillefer, *Phys. Rev. B* **86**, 140502 (2012).
- [12] S. L. Bud'ko, M. Sturza, D. Y. Chung, M. G. Kanatzidis, and P. C. Canfield, *Phys. Rev. B* **87**, 100509 (2013).
- [13] S. L. Bud'ko, D. Y. Chung, D. Bugaris, H. Claus, M. G. Kanatzidis, and P. C. Canfield, *Phys. Rev. B* **89**, 014510 (2014).
- [14] A. R. Moodenbaugh, Y. Xu, M. Suenaga, T. J. Folkerts, and R. N. Shelton, *Phys. Rev. B* **38**, 4596 (1988).
- [15] J. Paglione and R. L. Greene, *Nat. Phys.* **6**, 645 (2010).
- [16] D. C. Johnston, *Adv. Phys.* **59**, 803 (2010).
- [17] G. R. Stewart, *Rev. Mod. Phys.* **83**, 1589 (2011).
- [18] T. M. McQueen, A. J. Williams, P. W. Stephens, J. Tao, Y. Zhu, V. Ksenofontov, F. Casper, C. Felser, and R. J. Cava, *Phys. Rev. Lett.* **103**, 057002 (2009).
- [19] F.-C. Hsu, J.-Y. Luo, K.-W. Yeh, T.-K. Chen, T.-W. Huang, P. M. Wu, Y.-C. Lee, Y.-L. Huang, Y.-Y. Chu, D.-C. Yan, and M.-K. Wu, *Proc. Natl. Acad. Sci. USA* **105**, 14262 (2008).
- [20] K. Miyoshi, K. Morishita, E. Mutou, M. Kondo, O. Seida, K. Fujiwara, J. Takeuchi, and S. Nishigori, *J. Phys. Soc. Jpn.* **83**, 013702 (2014).
- [21] J.-F. Ge, Z.-L. Liu, C. Liu, C.-L. Gao, D. Qian, Q.-K. Xue, Y. Liu, and J.-F. Jia, *Nat. Mater.* **14**, 285 (2015).
- [22] T. Terashima, N. Kikugawa, S. Kasahara, T. Watashige, T. Shibauchi, Y. Matsuda, T. Wolf, A. E. Böhmer, F. Hardy, C. Meingast, H. v. Löhneysen, and S. Uji, *J. Phys. Soc. Jpn.* **84**, 063701 (2015).
- [23] M. Bendele, A. Amato, K. Conder, M. Elender, H. Keller, H.-H. Klauss, H. Luetkens, E. Pomjakushina, A. Raselli, and R. Khasanov, *Phys. Rev. Lett.* **104**, 087003 (2010).
- [24] M. Bendele, A. Ichsanow, Y. Pashkevich, L. Keller, T. Strässle, A. Gusev, E. Pomjakushina, K. Conder, R. Khasanov, and H. Keller, *Phys. Rev. B* **85**, 064517 (2012).
- [25] T. Imai, K. Ahilan, F. L. Ning, T. M. McQueen, and R. J. Cava, *Phys. Rev. Lett.* **102**, 177005 (2009).
- [26] F. F. Tafti, A. Juneau-Fecteau, M.-E. Delage, S. René de Cotret, J.-P. Reid, A. F. Wang, X.-G. Luo, X. H. Chen, N. Doiron-Leyraud, and L. Taillefer, *Nat. Phys.* **9**, 349 (2013).
- [27] T. Terashima, K. Kihou, K. Sugii, N. Kikugawa, T. Matsumoto, S. Ishida, C.-H. Lee, A. Iyo, H. Eisaki, and S. Uji, *Phys. Rev. B* **89**, 134520 (2014).
- [28] V. Taufour, N. Foroozani, M. A. Tanatar, J. Lim, U. Kaluarachchi, S. K. Kim, Y. Liu, T. A. Lograsso, V. G. Kogan, R. Prozorov, S. L. Bud'ko, J. S. Schilling, and P. C. Canfield, *Phys. Rev. B* **89**, 220509 (2014).
- [29] E. Helfand and N. R. Werthamer, *Phys. Rev.* **147**, 288 (1966).
- [30] T. Terashima, N. Kikugawa, A. Kiswandhi, D. Graf, E.-S. Choi, J. Brooks, S. Kasahara, T. Watashige, Y. Matsuda, T. Shibauchi, T. Wolf, A. E. Böhmer, F. Hardy, C. Meingast, H. v. Löhneysen, and S. Uji, [arXiv:1510.01840](https://arxiv.org/abs/1510.01840).
- [31] A. E. Böhmer, F. Hardy, F. Eilers, D. Ernst, P. Adelman, P. Schweiss, T. Wolf, and C. Meingast, *Phys. Rev. B* **87**, 180505 (2013).
- [32] M. A. Tanatar, N. Ni, G. D. Samolyuk, S. L. Bud'ko, P. C. Canfield, and R. Prozorov, *Phys. Rev. B* **79**, 134528 (2009).
- [33] M. A. Tanatar, N. Ni, C. Martin, R. T. Gordon, H. Kim, V. G. Kogan, G. D. Samolyuk, S. L. Bud'ko, P. C. Canfield, and R. Prozorov, *Phys. Rev. B* **79**, 094507 (2009).
- [34] S. L. Bud'ko, A. N. Voronovskii, A. G. Gapotchenko, and E. S. Itskevich, *Zh. Eksp. Teor. Fiz.* **86**, 778 (1984) [*Sov. Phys. JETP* **59**, 454 (1984)].
- [35] B. Bireckoven and J. Wittig, *J. Phys. E: Sci. Instrum.* **21**, 841 (1988).
- [36] S. K. Kim, M. S. Torikachvili, E. Colombier, A. Thaler, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **84**, 134525 (2011).
- [37] M. A. Tanatar, A. E. Böhmer, E. I. Timmons, M. Schütt, G. Drachuck, V. Taufour, S. L. Bud'ko, P. C. Canfield, R. M. Fernandes, and R. Prozorov, [arXiv:1511.04757](https://arxiv.org/abs/1511.04757).
- [38] S. Knöner, D. Zielke, S. Köhler, B. Wolf, T. Wolf, L. Wang, A. Böhmer, C. Meingast, and M. Lang, *Phys. Rev. B* **91**, 174510 (2015).
- [39] V. G. Kogan and R. Prozorov, *Rep. Prog. Phys.* **75**, 114502 (2012).
- [40] T. Terashima, N. Kikugawa, A. Kiswandhi, E.-S. Choi, J. S. Brooks, S. Kasahara, T. Watashige, H. Ikeda, T. Shibauchi, Y. Matsuda, T. Wolf, A. E. Böhmer, F. Hardy, C. Meingast, H. v. Löhneysen, M.-T. Suzuki, R. Arita, and S. Uji, *Phys. Rev. B* **90**, 144517 (2014).