

8-15-2015

Quantum oscillations in the heavy-fermion compound YbPtBi

E. Mun

Iowa State University and Ames Laboratory

Sergey L. Bud'ko

Iowa State University and Ames Laboratory, budko@ameslab.gov

Y. Lee

Iowa State University and Ames Laboratory

C. Martin

Iowa State University and Ames Laboratory

Makariy A. Tanatar

Iowa State University and Ames Laboratory, tanatar@ameslab.gov

See next page for additional authors

Follow this and additional works at: https://lib.dr.iastate.edu/physastro_pubs



Part of the [Condensed Matter Physics Commons](#)

The complete bibliographic information for this item can be found at https://lib.dr.iastate.edu/physastro_pubs/579.
For information on how to cite this item, please visit <http://lib.dr.iastate.edu/howtocite.html>.

This Article is brought to you for free and open access by the Physics and Astronomy at Iowa State University Digital Repository. It has been accepted for inclusion in Physics and Astronomy Publications by an authorized administrator of Iowa State University Digital Repository. For more information, please contact digirep@iastate.edu.

Quantum oscillations in the heavy-fermion compound YbPtBi

Abstract

We present quantum oscillations observed in the heavy-fermion compound YbPtBi in magnetic fields far beyond its field-tuned, quantum critical point. Quantum oscillations are observed in magnetic fields as low as 60 kOe at 60 mK and up to temperatures as high as 3 K, which confirms the very high quality of the samples as well as the small effective mass of the conduction carriers far from the quantum critical point. Although the electronic specific heat coefficient of YbPtBi reaches $\sim 7.4 \text{ J/molK}^2$ in zero field, which is one of the highest effective mass values among heavy-fermion systems, it is suppressed quickly by an applied magnetic field. The quantum oscillations were used to extract the quasiparticle effective masses of the order of the bare electron mass, which is consistent with the behavior observed in specific heat measurements. Such small effective masses at high fields can be understood by considering the suppression of Kondo screening.

Disciplines

Condensed Matter Physics

Comments

This article is published as Mun, E., S. L. Bud'ko, Y. Lee, C. Martin, M. A. Tanatar, R. Prozorov, and P. C. Canfield. "Quantum oscillations in the heavy-fermion compound YbPtBi." *Physical Review B* 92, no. 8 (2015): 085135. DOI: [10.1103/PhysRevB.92.085135](https://doi.org/10.1103/PhysRevB.92.085135). Posted with permission.

Authors

E. Mun, Sergey L. Bud'ko, Y. Lee, C. Martin, Makariy A. Tanatar, Ruslan Prozorov, and Paul C. Canfield



Quantum oscillations in the heavy-fermion compound YbPtBi

E. Mun,^{1,2} S. L. Bud'ko,¹ Y. Lee,¹ C. Martin,^{1,*} M. A. Tanatar,¹ R. Prozorov,¹ and P. C. Canfield¹

¹Ames Laboratory US DOE and Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50011, USA

²Department of Physics, Simon Fraser University, Burnaby, British Columbia, Canada V5A 1S6

(Received 29 June 2015; published 20 August 2015)

We present quantum oscillations observed in the heavy-fermion compound YbPtBi in magnetic fields far beyond its field-tuned, quantum critical point. Quantum oscillations are observed in magnetic fields as low as 60 kOe at 60 mK and up to temperatures as high as 3 K, which confirms the very high quality of the samples as well as the small effective mass of the conduction carriers far from the quantum critical point. Although the electronic specific heat coefficient of YbPtBi reaches ~ 7.4 J/mol K² in zero field, which is one of the highest effective mass values among heavy-fermion systems, it is suppressed quickly by an applied magnetic field. The quantum oscillations were used to extract the quasiparticle effective masses of the order of the bare electron mass, which is consistent with the behavior observed in specific heat measurements. Such small effective masses at high fields can be understood by considering the suppression of Kondo screening.

DOI: [10.1103/PhysRevB.92.085135](https://doi.org/10.1103/PhysRevB.92.085135)

PACS number(s): 71.18.+y, 71.27.+a, 75.30.Mb, 71.10.Hf

I. INTRODUCTION

Heavy-fermion (HF) compounds have provided some of the clearest evidence for quantum phase transitions [1]. A large effective mass introduces a characteristic low energy scale that can easily be tuned by nonthermal control parameters, making HF systems desirable for studying quantum criticality. An antiferromagnetic (AFM) quantum critical point (QCP) has been explored in many HF systems [2,3]. However, a magnetic field-tuned QCP in Yb-based materials has been limited to only a few cases, among stoichiometric compounds, in particular, tetragonal YbRh₂Si₂ [4] and hexagonal YbAgGe [5]. Recently, the HF compound YbPtBi attracted attention because of a quantum phase transition driven by the magnetic field [6], in particular, providing relatively easy access to the field-tuned QCP as well as the appearance of a new phase between the ordered (AFM) state and paramagnetic Fermi liquid state.

YbPtBi has a face-centered-cubic ($F\bar{4}3m$) structure and manifests AFM ordering below $T_N = 0.4$ K with an electronic specific heat coefficient of $\gamma \sim 7.4$ J/mol K² at zero field [6,7]. Recent neutron scattering experiments characterized the averaged ordered moment of $\sim 0.8 \mu_B/\text{Yb}$ with the AFM propagation vector $\tau = (1/2, 1/2, 1/2)$ [8]. A field-tuned QCP is readily accessible by suppressing AFM ordering below $T_N = 0.4$ K by application of an external magnetic field of $H_c \sim 4$ kOe [6]. The temperature dependence of the resistivity indicates a recovery of the Fermi liquid (FL) state for $H^* \gtrsim 7.8$ kOe. In addition, of particular interest in YbPtBi is the fact that a new phase appears in the proximity of the QCP. In this new phase, strange metallic behavior (non-Fermi liquid) manifests and separates the AFM state and FL regime. A crossover scale has been found in thermodynamic and transport measurements [6], where the crossover line shows a tendency of converging to $H^* \sim 7.8$ kOe in the zero temperature limit. A similar phase near QCP and the crossover line have been observed in YbAgGe [9,10] and Ge-doped YbRh₂Si₂ [11].

Although many examples of QCP have been reported in HF materials [2,3], theoretical classifications have not been firmly established yet. Unlike the traditional picture (e.g., for a spin density wave) of approaching a quantum criticality [12–14], where the heavy quasiparticles survive near the QCP, the unconventional way (local quantum criticality) of explaining the quantum phase transition suggests a destruction of the Kondo screening of the f electrons [15–17], involving Fermi surface reconstruction, where the heavy quasiparticles decompose into the conduction sea and local magnetic moments. If the Fermi surfaces have different shapes or are completely reconstructed across the QCP, then a Lifshitz transition, associated with a reconstruction of the Fermi surface, must separate the two phases between the ordered and disordered state. In general, because most of the HF compounds have multiple Fermi surfaces, it is difficult to probe such a Lifshitz transition at extremely low temperatures. Transport measurements can address this issue clearly for a system with a single band, however, this may not be true for multiband systems. In metallic systems, the interpretation of physical quantities requires careful consideration of the Fermi surface, especially at the QCP.

In this paper, we report the determination of the high-field stabilized Fermi surfaces for YbPtBi inferred from quantum oscillations and band structure calculations. By producing high quality single crystals, we are able to infer Fermi surfaces by detecting quantum oscillations above ~ 60 kOe at 60 mK in resistivity measurements.

In principle, the Fermi surface can be studied by comparing the quantum oscillation measurements with electronic structure calculations. However, quantum oscillation data in most HF compounds are likely to be incomplete, mainly due to the experimental difficulties. This is a standing problem in HF physics: In order to detect the heavier effective masses, higher magnetic fields and extremely lower temperatures (order of \sim mK) are needed, however, the mass enhancement can be suppressed due to the application of these larger magnetic fields. Further, when there is a $4f$ electron contribution to the Fermi volume, band structure calculations cannot accurately estimate the many-body-enhanced density of states and sometimes fail to predict the Fermi surface topology in

*Present address: Ramapo College of New Jersey, Mahwah, NJ 07430, USA.

detail. Therefore, in this study, we focused the data analysis on the high-field paramagnetic regime and compared it to the band structure calculations in zero field for simple, trivalent Yb. We confirm the multiband nature of this system, but are unable to identify the Fermi surface with heavy masses. In addition, we compare our results to the family of $R\text{PtBi}$, where quantum oscillations have been observed for $R = \text{Y, La, Ce, and Nd}$ [18–21].

II. EXPERIMENT

Single crystals of YbPtBi were grown out of a ternary melt with an excess of Bi, as has been described in earlier reports [22,23]. Four-probe ac resistivity ($f = 16$ Hz) measurements were performed in a Oxford dilution refrigerator, where the samples were attached to the cold stage using GE varnish. Pt wires were used as leads and attached to the sample with Epotek H20E silver epoxy. The magnetic field (\mathbf{H}) was applied along the [100] and [111] directions, and the electric current (\mathbf{I}) across the sample was applied perpendicular to \mathbf{H} : $\mathbf{H} \perp \mathbf{I}$. Details of the experimental conditions are given in Ref. [6].

In order to compare the experimental observations of Shubnikov–de Haas frequencies to the topology of the Fermi surfaces, we calculated the zero field band structure of paramagnetic, trivalent YbPtBi. For the Fermi surface calculation, we have used a full-potential linear augmented plane-wave (FP-LAPW) [24] method with a local density functional [25]. The structure data were taken from reported experimental results [26]. To obtain the self-consistent charge density, we chose 1204 k points in the irreducible Brillouin zone and set $R_{\text{MT}}K_{\text{max}}$ to 9.0, where R_{MT} is the smallest muffin-tin radius and K_{max} is the plane-wave cutoff. We used muffin-tin radii 2.5 for all Yb, Bi, and Pt atoms. The calculation was iterated with 0.0001 electrons of charge and 0.01 mRy of total energy convergence criteria. Although there was a discussion about $4f$ electron pinning at the Fermi energy [27] and we were aware that the Fermi surface is quite different under the influence of $4f$ electrons, [28] we treated $4f$ electrons as core electrons since we were interested in the high magnetic field, paramagnetic state. To obtain Shubnikov–de Haas oscillations frequencies we calculated two-dimensional Fermi surfaces and integrated the Fermi surface area. We chose planes which were perpendicular to the k_z axis and had a 0.01 ($2\pi/a$) interval. Each plane ($-1 \leq k_x, k_y \leq 1$) was divided with 100×100 mesh. For a three-dimensional Fermi surface, we used 2300 k points in the irreducible Brillouin zone and a XcrysDen graphic program [29].

III. RESULT

Shubnikov–de Haas (SdH) quantum oscillations have been observed throughout the magnetoresistance (MR) measurements at low temperatures and high magnetic fields. Figure 1 shows the MR at $T = 0.1$ K for a magnetic field applied along the [100] and [111] directions. An anomaly shown in MR below 10 kOe is related to the suppression of AFM ordering, as shown in Ref. [6]. For $H > 20$ kOe, a broad local extremum in MR is observed for both magnetic field directions: a local maximum around 45 kOe for $\mathbf{H} \parallel [111]$ and a local minimum around 30 kOe for $\mathbf{H} \parallel [100]$. This

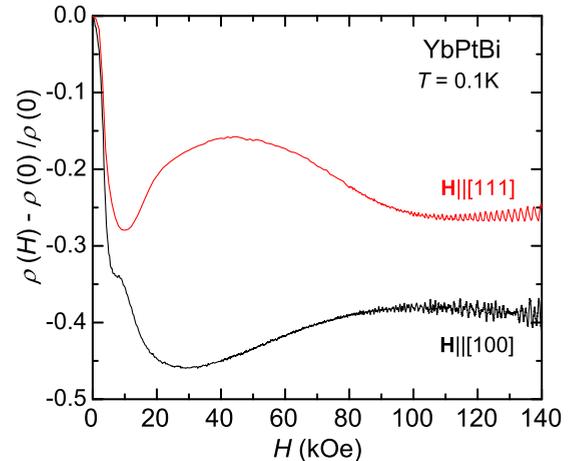


FIG. 1. (Color online) Magnetoresistance (MR), plotted as $[\rho(H) - \rho(0)]/\rho(0)$ vs H , of YbPtBi at $T = 0.1$ K along $\mathbf{H} \parallel [100]$ and $\mathbf{H} \parallel [111]$. Quantum oscillations are discernible for both curves at high magnetic fields.

behavior may be due to the change in scattering processes with crystalline-electric-field (CEF) levels, or it may be the oscillatory component corresponding to an extremely small Fermi surface area in which the extremely small frequency has been observed for NdPtBi [21] in the paramagnetic state. For YbPtBi, though, this is not likely to be the case because the frequency is so small that it would have an amplitude that would make it hard to observe in SdH measurements. What is unambiguous are the clear quantum oscillations at high magnetic fields.

In Figs. 2(a) and 2(c) typical SdH data sets for YbPtBi, after subtracting the background contributions, are displayed as a function of $1/H$ at selected temperatures. The amplitude of the oscillations decreases as the temperature increases. Since the signals comprise a superposition of several oscillatory components, the data are most easily visualized by using a fast Fourier transform (FFT), as shown in Fig. 2(b) for $\mathbf{H} \parallel [100]$ and Fig. 2(d) for $\mathbf{H} \parallel [111]$. The FFT spectra at $T = 0.06$ K show several frequencies, including, in the case of $\mathbf{H} \parallel [100]$, second harmonics with very small amplitudes. The observed frequencies are summarized in Table I.

Quantum oscillations are observed in magnetic fields as low as 60 kOe at the lowest temperature measured and at temperatures as high as 3 K, which further confirms the very high quality of the samples as well as the relatively small effective masses of the associated conduction electrons. The frequencies in FFT spectra do not shift with temperature and most of the first harmonics of the frequencies are clearly observed as high as 2 K.

The oscillation amplitudes and the fit curves using the temperature reduction factor are plotted in Figs. 3(a) and 3(b). The cyclotron effective masses m^* of the carriers from the various orbits were determined by fitting the temperature-dependent amplitude of the oscillations to the Lifshitz-Kosevich (LK) formula [30] for each frequency. The calculated effective masses range from $m^*(\alpha) \sim 1.41 m_e$ to $m^*(\xi_1) \sim 0.49 m_e$, where m_e is the bare electron mass. The inferred effective masses are summarized in Table I. We were not able to

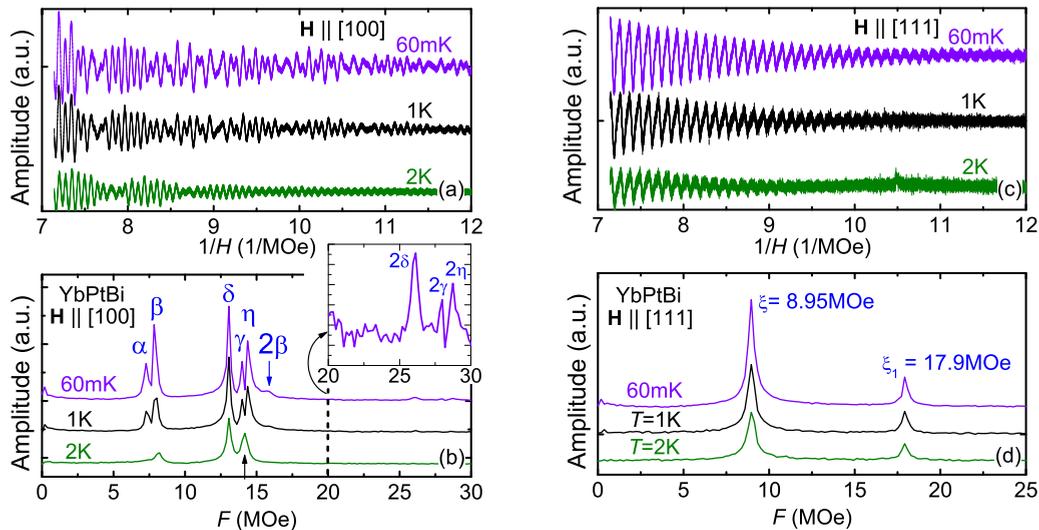


FIG. 2. (Color online) SdH of YbPtBi at $T = 0.06, 1,$ and 2 K, plotted after subtracting the background MR, for (a) $\mathbf{H} \parallel [100]$ and (c) $\mathbf{H} \parallel [111]$. FFT spectra of SdH data at $T = 0.06, 1,$ and 2 K for (b) $\mathbf{H} \parallel [100]$ and (d) $\mathbf{H} \parallel [111]$.

estimate the effective masses, associated with the second harmonic frequencies, due to the small amplitude of the signals. Although the frequency ξ_1 is an integer multiple of ξ , $\xi_1 \simeq 2\xi$, it does not appear to be a higher harmonic of ξ because of the inconsistent effective masses. In addition, if these frequencies are originating from the same extremal orbit, the phase difference between two frequencies cannot be explained; the oscillation curves are generated by the LK formula with the phase term $A_1 \sin(2\pi\xi/H + \pi/1.95) + A_2 \sin(2\pi\xi_1/H - \pi/7.7)$, as shown in Fig. 3(c). Therefore, ξ_1 really appears to be an independent frequency, coming from different extremal orbits. The frequency of the orbit η is almost twice the frequency of the α , however, these orbits also apparently come from different Fermi surfaces. If the orbit η is the second harmonics of the α , the oscillation amplitude of the η should be smaller than that of α , but the amplitudes of these frequencies are almost the same. Therefore, the orbit η is not a second harmonic of α . Note that the frequency, observed near 14 MOe at 2 K along $\mathbf{H} \parallel [100]$, seems to split from one

component into two components of γ and η with decreasing temperature, as indicated by the up arrow in Fig. 2(b). At present, it is not clear whether the two frequencies of γ and η originate from the same extremal orbit, and thus it needs to be clarified by further detailed measurements.

IV. DISCUSSION

The low carrier density for YbPtBi, determined from Hall coefficient measurements [6], implies a Fermi surface

TABLE I. Frequencies f and effective masses m^* obtained from the SdH oscillations. m_e is the bare electron mass.

	f (MOe)	m^*/m_e	
$\mathbf{H} \parallel [100]$	α	7.27	1.41
	β	7.83	1.59
	δ	13.06	0.83
	γ	13.99	0.80
	η	14.37	0.97
	2β	15.67	
	2δ	26.13	
	2γ	27.99	
	2η	28.74	
$\mathbf{H} \parallel [111]$	ξ	8.95	1.22
	ξ_1	17.90	0.49

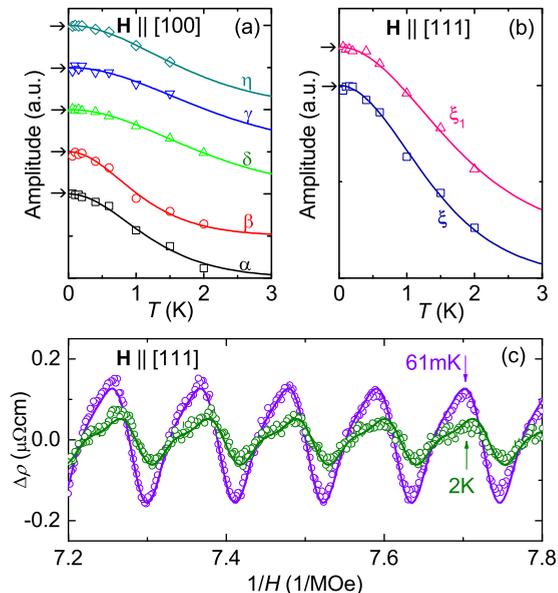


FIG. 3. (Color online) (a), (b) Temperature dependence of the SdH amplitudes. Solid lines represent the fit curves to the Lifshitz-Kosevich (LK) formula. All data and fit curves are normalized to 1, indicated by horizontal arrows, and shifted for clarity. (c) Resistivity along $\mathbf{H} \parallel [111]$ at $T = 0.06$ and 1 K, plotted as a function of $1/H$ after subtracting the background MR, where the solid lines represent the fit curves based on the LK formula with the frequency ξ and ξ_1 .

occupying a small portion of the Brillouin zone, which is consistent with the results of our analysis of the quantum oscillations. The frequency of the quantum oscillations is proportional to the extremal cross section A_{FS} of the Fermi surface, $f = (\hbar/2\pi e)A_{FS}$ [30]. In the high-field paramagnetic region, direct evidence for small Fermi surfaces comes from SdH measurements, where several small extremal orbits, implying an occupation of a small portion of the Brillouin zone, are observed. Quantum oscillations have also been observed for LaPtBi and CePtBi [19,20] from the electrical resistivity measurements in pulsed magnetic fields up to 50 T. The oscillation frequencies for LaPtBi are approximately ten times smaller, 0.65 MOe for $\mathbf{H} \parallel [100]$ increasing to 0.95 MOe for $\mathbf{H} \parallel [110]$, than for YbPtBi. In this family, SdH for YPtBi is observed up to 10 K with a frequency of 0.46 MOe [18]. Note that a single SdH oscillation with $f = 0.0074$ MOe was inferred from magnetoresistance measurements in NdPtBi [21], where the observed frequency is two orders of magnitude smaller than the frequencies observed for other compounds in this family. It is not clear whether the origin of the extraordinarily small frequency for NdPtBi is related to the broad local extrema observed in YbPtBi (Fig. 1). For CePtBi the anomalous temperature dependence of the SdH frequency, $f = 0.6$ MOe, was observed along $\mathbf{H} \parallel [100]$, and a very low SdH frequency of ~ 0.2 MOe, which is independent of temperature, was found along $\mathbf{H} \parallel [111]$. In addition to the unusual temperature dependence of the SdH frequency for CePtBi, the disappearance of the oscillations was observed above about 25 T, at which the magnetic field-induced band structure change was proposed [20].

Since the SdH frequencies for YbPtBi are not changed by the temperature or magnetic field, within the temperature and magnetic field range of our measurements, such a band structure modification is not expected. The band calculations for LaPtBi [31] and CePtBi [19], assuming localized $4f$ states, were found to be semimetals. In these calculations, two holelike Fermi surface sheets are found around the zone center, which are similar to the measured angular dependences of the Fermi surface cross-section areas of LaPtBi. A number of small electronlike pockets are also predicted in the band calculations. The effective masses for both LaPtBi and CePtBi have been estimated to be $\sim 0.3 m_e$ [20], which is somewhat smaller than for YbPtBi. The observed trend of SdH frequencies suggests larger Fermi surface sheets for YbPtBi than for LaPtBi, and these are consistent with the earlier resistivity results of RPtBi [22], where the resistivity varied from metallic (semimetallic) to small gap semiconductor when the rare earth changed from Lu to Nd [22]; $\rho(T)$ of LuPtBi decreases and $\rho(T)$ of NdPtBi increases as the temperature decreases. The carrier density for LuPtBi is approximately two orders of magnitude bigger than that for LaPtBi [6].

The results of band structure calculations are shown in Fig. 4(a). The overall features are very similar to the results of LaPtBi, however, with a larger Fermi surface occupation of the Brillouin zone. Around the zone center, two holelike Fermi surfaces (bands 55 and 56) are surrounded by 16 small electronlike pockets (bands 57 and 58). These calculated Fermi surfaces of YbPtBi are plotted in Figs. 4(b) and 4(c). The SdH frequencies of these four bands are calculated to be 2.4, 3.5, 0.79, and 0.65 MOe from the maximum area perpendicular

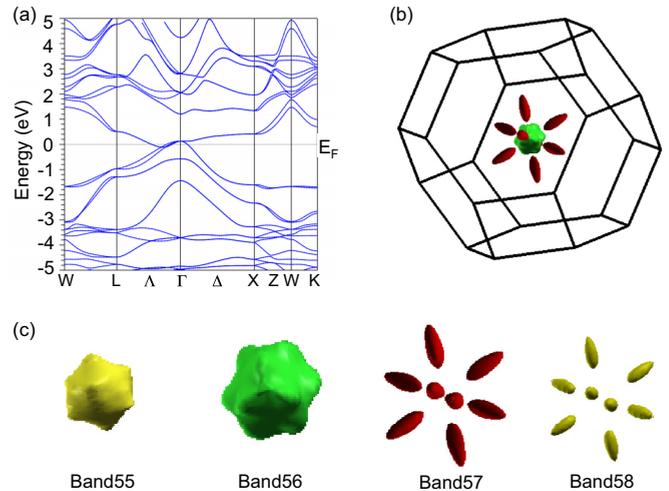


FIG. 4. (Color online) (a) Band structure of nonmagnetic YbPtBi, calculated for localized $4f$ states. (b) Calculated Fermi surface in the fcc Brillouin zone. Two three-dimensional pockets (bands 55 and 56), located in the zone center, are surrounded by 16 cigar-shaped pockets (bands 57 and 58). (c) Enlarged Fermi surfaces for bands 55, 56, 57, and 58.

to the applied magnetic field direction, where there are orbits very close to 2.4 and 3.5 MOe due to the three-dimensional shape of the Fermi surfaces at the zone center. These values are much larger than the predicted values for LaPtBi and CePtBi [19,20], however, they are four times smaller than the frequencies determined from our experimental results.

The Fermi surfaces of YbPtBi are highly sensitive to the $4f$ electron contributions, as predicted in Ref. [28]. When the $4f$ electrons are included in the band calculations, the six holelike pockets are located in the zone center in which the predicted frequencies range from ~ 27 to ~ 164 MOe [28], which is much higher than the experimental observations. So, treating $4f$ electrons as included in the core levels appears to be reasonable. If the Fermi level is shifted to a lower energy, the experimentally observed frequencies can be matched to the holelike pockets at the zone center, whereas the electronlike pocket surrounding the zone center will not be detected. As a conjecture, the effective masses and frequencies of the orbits α and β along the $[100]$ direction, compared to those of ξ along the $[111]$ direction, are almost the same, suggesting that these orbits all arise from band 55. Similarly, the orbits δ , γ , and η , compared to ξ_1 , could all arise from the three-dimensional band 56. Without an angular dependence of the SdH measurements, the Fermi surface topology cannot be determined unambiguously, and further theoretical work is needed to unravel the discrepancies in the precise extremal orbit sizes.

Since we have observed only small effective masses for YbPtBi, it is expected that the hybridization between $4f$ and conduction electrons has been suppressed for these high magnetic fields. This is consistent with the specific heat results; the enormous value of $\gamma \sim 7.4$ J/mol K² for $H = 0$ is suppressed to $\gamma \sim 0.15$ J/mol K² for $H = 50$ kOe and would extrapolate to ~ 0.030 J/mol K² at 140 kOe (using data from Ref. [6]). Note that if there are still significant $4f$ electron contributions in this magnetic field range, up to 140 kOe,

it would require much lower temperatures to observe heavy electrons in the SdH measurements. This is a standing problem in HF physics, that in order to detect the heavier effective masses, higher magnetic fields and very low temperatures are needed, however, the mass enhancement can be suppressed due to the application of these larger magnetic fields. Thus, lower measurement temperatures and crystals with extremely low scattering in terms of the Dingle temperature are necessary to detect the heavier effective mass of the carriers. Measuring de Haas–van Alphen (dHvA) oscillations as a complement to SdH oscillations may be another experimental approach, since oscillation amplitudes have different dependences of m^* in dHvA and SdH. However, this task can be challenging due to the high paramagnetic background signal.

V. SUMMARY

In summary, we have presented Shubnikov–de Haas quantum oscillations detected in YbPtBi. The band structure calculations for the Fermi surface were also presented, where treating $4f$ electrons as included in core levels appears to be important in the high-field regime far beyond the quantum

critical point. A comparison was made between the high-field oscillations and zero-field band structure calculations, which allowed us to infer Fermi surfaces only in the paramagnetic state. The current study clearly shows that (i) small oscillation frequencies suggest a low carrier density, consistent with Hall effect measurements, (ii) multiple oscillation frequencies imply a multiband nature, and (iii) small effective masses at high fields indicate a suppression of Kondo screening, consistent with specific heat results. Although it was not possible to infer a heavy-fermion state, the current study may, in the future, give useful information about the nature of the quantum criticality when the Fermi volumes at low fields are available.

ACKNOWLEDGMENTS

This work was supported by the US Department of Energy, Office of Basic Energy Science, Division of Materials Sciences and Engineering. The research was performed at the Ames Laboratory. Ames Laboratory is operated for the US Department of Energy by Iowa State University under Contract No. DE-AC02-07CH11358. The work at Simon Fraser University was supported by the Natural Sciences and Engineering Research Council of Canada.

-
- [1] H. v. Löhneysen, A. Rosch, M. Vojta, and P. Wölfle, *Rev. Mod. Phys.* **79**, 1015 (2007).
- [2] G. R. Stewart, *Rev. Mod. Phys.* **73**, 797 (2001).
- [3] G. R. Stewart, *Rev. Mod. Phys.* **78**, 743 (2006).
- [4] P. Gegenwart, J. Custers, C. Geibel, K. Neumaier, T. Tayama, K. Tenya, O. Trovarelli, and F. Steglich, *Phys. Rev. Lett.* **89**, 056402 (2002).
- [5] S. L. Bud'ko, E. Morosan, and P. C. Canfield, *Phys. Rev. B* **69**, 014415 (2004).
- [6] E. D. Mun, S. L. Bud'ko, C. Martin, H. Kim, M. A. Tanatar, J.-H. Park, T. Murphy, G. M. Schmiedeshoff, N. Dilley, R. Prozorov, and P. C. Canfield, *Phys. Rev. B* **87**, 075120 (2013).
- [7] Z. Fisk, P. C. Canfield, W. P. Beyermann, J. D. Thompson, M. F. Hundley, H. R. Ott, E. Felder, M. B. Maple, M. A. Lopez de la Torre, P. Visani, and C. L. Seaman, *Phys. Rev. Lett.* **67**, 3310 (1991).
- [8] B. G. Ueland, A. Kreyssig, K. Prokeš, J. W. Lynn, L. W. Harriger, D. K. Pratt, D. K. Singh, T. W. Heitmann, S. Sauerbrei, S. M. Saunders, E. D. Mun, S. L. Bud'ko, R. J. McQueeney, P. C. Canfield, and A. I. Goldman, *Phys. Rev. B* **89**, 180403(R) (2014).
- [9] S. L. Bud'ko, V. Zapf, E. Morosan, and P. C. Canfield, *Phys. Rev. B* **72**, 172413 (2005).
- [10] E. Mun, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **82**, 174403 (2010).
- [11] J. Custers, P. Gegenwart, C. Geibel, F. Steglich, P. Coleman, and S. Paschen, *Phys. Rev. Lett.* **104**, 186402 (2010).
- [12] J. A. Hertz, *Phys. Rev. B* **14**, 1165 (1976).
- [13] A. J. Millis, *Phys. Rev. B* **48**, 7183 (1993).
- [14] T. Moriya and T. Takimoto, *J. Phys. Soc. Jpn.* **64**, 960 (1995).
- [15] Q. Si, S. Rabello, K. Ingersent, and J. L. Smith, *Nature (London)* **413**, 804 (2001).
- [16] Q. Si, S. Rabello, K. Ingersent, and J. L. Smith, *Phys. Rev. B* **68**, 115103 (2003).
- [17] P. Coleman, *Handbook of Magnetism and Advanced Magnetic Materials* (Wiley, Hoboken, NJ, 2007), Vol. 1.
- [18] N. P. Butch, P. Syers, K. Kirshenbaum, A. P. Hope, and J. Paglione, *Phys. Rev. B* **84**, 220504(R) (2011).
- [19] G. Goll, J. Hagel, H. v. Löhneysen, T. Pietrus, S. Wanka, J. Wosnitzer, G. Zwirgagl, T. Yoshino, T. Takabatake, and A. G. M. Jansen, *Europhys. Lett.* **57**, 233 (2002).
- [20] J. Wosnitzer, G. Goll, A. D. Bianchi, B. Bergk, N. Kozlova, I. Opahle, S. Elgazzar, M. Richter, O. Stockert, H. v. Löhneysen, T. Yoshino, and T. Takabatake, *New J. Phys.* **8**, 174 (2006).
- [21] D. T. Morelli, P. C. Canfield, and P. Drymiotis, *Phys. Rev. B* **53**, 12896 (1996).
- [22] P. C. Canfield, J. D. Thompson, W. P. Beyermann, A. Lacerda, M. F. Hundley, E. Peterson, Z. Fisk, and H. R. Ott, *J. Appl. Phys.* **70**, 5800 (1991).
- [23] P. C. Canfield and Z. Fisk, *Philos. Mag. B* **65**, 1117 (1992).
- [24] P. Blaha, K. Schwarz, G. K. H. Madsen, D. Kvasnick, and J. Luitz, *WIEN2k, An Augmented Plane wave + Local Orbitals Program for Calculation Crystal Properties* (K. Schwarz, TU Wien, Austria, 2001).
- [25] J. P. Perdew and Y. Wang, *Phys. Rev. B* **45**, 13244 (1992).
- [26] R. A. Robinson, A. Purwanto, M. Kohgi, P. C. Canfield, T. Kamiyama, T. Ishigaki, J. W. Lynn, R. Erwin, E. Peterson, and R. Movshovich, *Phys. Rev. B* **50**, 9595 (1994).
- [27] P. M. Oppeneer, V. N. Antonov, A. N. Yaresko, A. Ya. Perlov, and H. Eschrig, *Phys. Rev. Lett.* **78**, 4079 (1997).
- [28] G. J. McMullan and M. P. Ray, *J. Phys.: Condens. Matter* **4**, 7095 (1992).
- [29] <http://www.xcrysden.org>
- [30] D. Shoenberg, *Magnetic Oscillations in Metals* (Cambridge University Press, Cambridge, UK, 1984).
- [31] T. Oguchi, *Phys. Rev. B* **63**, 125115 (2001).