

3-18-2013

## A search for field-induced ordering in the optimally doped Ba(Fe, Co)(2)As-2 superconductor

Katherine Quinn  
*McGill University*

D. H. Ryan  
*McGill University*

Paul C. Canfield  
*Iowa State University and Ames Laboratory, canfield@ameslab.gov*

Sergey L. Bud'ko  
*Iowa State University and Ames Laboratory, budko@ameslab.gov*

J. M. Cadogan  
*UNSW Canberra*

Follow this and additional works at: [https://lib.dr.iastate.edu/physastro\\_pubs](https://lib.dr.iastate.edu/physastro_pubs)



Part of the [Condensed Matter Physics Commons](#)

---

The complete bibliographic information for this item can be found at [https://lib.dr.iastate.edu/physastro\\_pubs/612](https://lib.dr.iastate.edu/physastro_pubs/612).  
For information on how to cite this item, please visit <http://lib.dr.iastate.edu/howtocite.html>.

This Article is brought to you for free and open access by the Physics and Astronomy at Iowa State University Digital Repository. It has been accepted for inclusion in Physics and Astronomy Publications by an authorized administrator of Iowa State University Digital Repository. For more information, please contact [digirep@iastate.edu](mailto:digirep@iastate.edu).

---

## A search for field-induced ordering in the optimally doped Ba(Fe, Co)(2)As-2 superconductor

### Abstract

A Fe-57 Mossbauer search for field-induced magnetic order in optimally doped Ba(Fe<sub>1-x</sub>Co<sub>x</sub>)(2)As-2 in fields of up to 6 T showed no changes that could be attributed to field-induced order. We also observed no difference between the normal (30 K) and superconducting states (5 K). Any field-induced order is certainly less than 1% of the order present in the parent BaFe<sub>2</sub>As<sub>2</sub>.

### Disciplines

Condensed Matter Physics

### Comments

This article may be downloaded for personal use only. Any other use requires prior permission of the author and AIP Publishing. This article appeared in Quinn, Katherine, D. H. Ryan, P. C. Canfield, S. L. Bud'ko, and J. M. Cadogan. "A search for field-induced ordering in the optimally doped Ba (Fe, Co) 2 As 2 superconductor." *Journal of Applied Physics* 113, no. 17 (2013): 17E127, and may be found at DOI: [10.1063/1.4795421](https://doi.org/10.1063/1.4795421). Posted with permission.

# A search for field-induced ordering in the optimally doped $\text{Ba}(\text{Fe}, \text{Co})_2\text{As}_2$ superconductor

Cite as: J. Appl. Phys. **113**, 17E127 (2013); <https://doi.org/10.1063/1.4795421>

Submitted: 23 October 2012 . Accepted: 07 December 2012 . Published Online: 18 March 2013

Katherine Quinn, D. H. Ryan, P. C. Canfield, S. L. Bud'ko, and J. M. Cadogan



View Online



Export Citation



CrossMark

## ARTICLES YOU MAY BE INTERESTED IN

**Perspective: Sloppiness and emergent theories in physics, biology, and beyond**

The Journal of Chemical Physics **143**, 010901 (2015); <https://doi.org/10.1063/1.4923066>

**Magnetic and structural transitions in the iron-chalcogenide high- $T_c$  superconductor:  $\text{K}_{0.8}\text{Fe}_{1.76}\text{Se}_{2.00}$**

Journal of Applied Physics **111**, 07E126 (2012); <https://doi.org/10.1063/1.3673848>

**Making sense of the Legendre transform**

American Journal of Physics **77**, 614 (2009); <https://doi.org/10.1119/1.3119512>

Lock-in Amplifiers  
Find out more today



Zurich  
Instruments



# A search for field-induced ordering in the optimally doped $\text{Ba}(\text{Fe}, \text{Co})_2\text{As}_2$ superconductor

Katherine Quinn,<sup>1</sup> D. H. Ryan,<sup>1,a)</sup> P. C. Canfield,<sup>2</sup> S. L. Bud'ko,<sup>2</sup> and J. M. Cadogan<sup>3</sup>

<sup>1</sup>Physics Department and Centre for the Physics of Materials, McGill University, 3600 University Street, Montreal, Quebec H3A 2T8, Canada

<sup>2</sup>Ames Laboratory and Department of Physics and Astronomy, Iowa State University, Ames, Iowa 50010, USA

<sup>3</sup>School of Physical, Environmental and Mathematical Sciences, UNSW Canberra, Canberra ACT 2610, Australia

(Presented 15 January 2013; received 23 October 2012; accepted 7 December 2012; published online 18 March 2013)

A  $^{57}\text{Fe}$  Mössbauer search for field-induced magnetic order in optimally doped  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  in fields of up to 6 T showed no changes that could be attributed to field-induced order. We also observed no difference between the normal (30 K) and superconducting states (5 K). Any field-induced order is certainly less than 1% of the order present in the parent  $\text{BaFe}_2\text{As}_2$ . © 2013 American Institute of Physics. [<http://dx.doi.org/10.1063/1.4795421>]

## I. INTRODUCTION

Transverse-field muon spin relaxation (TF- $\mu\text{SR}$ ) is routinely used to determine the magnetic penetration depth ( $\lambda$ ) of type-II superconductors. The superconducting sample is placed in an applied field, the field distribution ( $n(\mathbf{B})$ ) within the sample is measured, and then the contribution of the vortex lattice is modelled to obtain  $\lambda$ . An underlying weakness of this method is that the actual geometry of the vortex lattice, the vortex structure, and vortex interactions may not be known with sufficient certainty. Furthermore, one must assume that other contributions to  $n(\mathbf{B})$  are absent. Recent work on the iron-based superconductors  $\text{Sr}(\text{Fe}_{0.91}\text{Co}_{0.09})_2\text{As}_2$ <sup>1,2</sup> and  $\text{Ba}(\text{Fe}_{0.91}\text{Co}_{0.09})_2\text{As}_2$ <sup>2,3</sup> has led to the suggestion that the applied field may induce magnetic order in these systems, and that the presence of field-induced order in the vortex cores, where superconductivity has been suppressed, may affect the derived penetration depth.<sup>3</sup> Such field-induced ordering may be possible as the parent  $\text{BaFe}_2\text{As}_2$  exhibits spin density wave ordering at 143 K,<sup>4</sup> and magnetic order persists in Co-doped  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  as far as  $x = 5.5\%$ .<sup>5,6</sup>

As a frequency-domain technique, many variants of  $\mu\text{SR}$  are most suited to the observation of small fields and moments and therefore tend to be carried out with small applied fields (typically tens of mT). The observed field shifts leading to the suggestion of field-induced order are also small (of order a few percent of the applied field in most cases). Mössbauer spectroscopy, being an energy-domain technique, is more sensitive to larger fields and the ordering in the parent phase is quite significant.<sup>7</sup> Furthermore, since any induced moment is likely to be associated with the iron atoms, a direct probe of these sites should be more sensitive than an impurity-based technique like  $\mu\text{SR}$ . We therefore set out to investigate whether any evidence of field-induced order could be found in optimally doped  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  at larger applied fields.

## II. EXPERIMENTAL METHODS

Single-crystals of  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  with  $x = 0\%$ , 4.7%, 7.4%, and 7.7%, were grown using a self-flux method.<sup>8</sup> The crystals were roughly square plates, with dimensions 5 mm  $\times$  5 mm  $\times$  0.5 mm and the crystal  $c$ -axis normal to the plate surface. Susceptibility and magnetisation measurements using a quantum design physical property measurement system confirmed that the three cobalt-doped samples were superconducting and that all magnetic and superconducting transitions were consistent with the earlier reports.<sup>8–10</sup> The samples with  $x = 7.4\%$  and 7.7% were found to be close to optimally doped with superconducting transition temperatures of  $\sim 21$  K.

The samples for the Mössbauer work were prepared by cleaving the crystals into thin sheets along the  $ab$ -plane with a razor blade and making a 1.5–2 cm<sup>2</sup> mosaic, with tungsten-loaded GE-7031 varnish used to fill any gaps between the crystals. Low temperature  $^{57}\text{Fe}$  Mössbauer spectra were obtained using a helium flow cryostat equipped with a 7 T split-coil superconducting solenoid. The 50 mCi  $^{57}\text{Co}$   $\text{Rh}$  source was located at a null point in the field, with the drive, source, and sample mounted vertically and operated in sine mode. Spectra were initially fitted using a simple first-order perturbation code; however, the effects of a small, unresolved quadrupole splitting led us to use a full solution to the Hamiltonian for the  $m_I = \frac{3}{2} \rightarrow \frac{1}{2}$  transition, modified for single-crystals. No attempt was made to include the effects of the incommensurate spin density wave ordering of  $\text{BaFe}_2\text{As}_2$  in fitting its spectrum.<sup>7</sup>

Zero-field spectra taken at 5 K and shown in Figure 1 confirm that magnetic order is lost as cobalt is added. The two optimally doped samples show no magnetic splitting at 5 K.

## III. RESULTS

Spectra taken in large applied magnetic fields show a clear magnetic splitting for both the 7.4% (Figure 2) and the 7.7% (Figure 3) samples. As the field was applied parallel to the  $\gamma$ -beam (and the crystal  $c$ -axis) the two  $\Delta m_I = 0$  transitions (normally lines 2 and 5 of the 6-line Zeeman pattern for  $^{57}\text{Fe}$  in a magnetic field) have zero intensity and only

<sup>a)</sup>Author to whom correspondence should be addressed. Electronic mail: dhryan@physics.mcgill.ca.

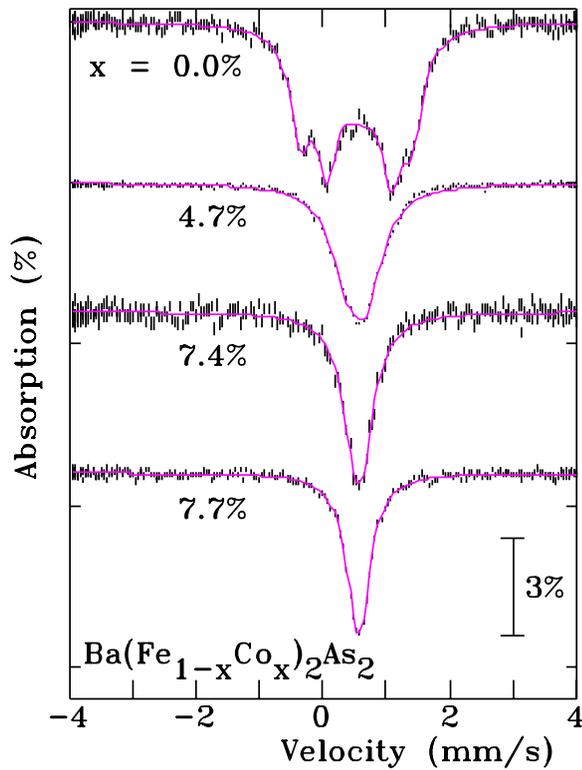


FIG. 1. Mössbauer spectra for a single-crystal mosaic of  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  at 5 K in zero applied field. There is no magnetic splitting for  $x = 7.4\%$  and  $7.7\%$ .

four lines (1–3–4–6) are seen. There is also a clear asymmetry to line intensities in the spectra, most evident in the central doublets (lines 3 and 4) in the middle field range (1–4 T) spectra. This is the result of a small, unresolved quadrupole

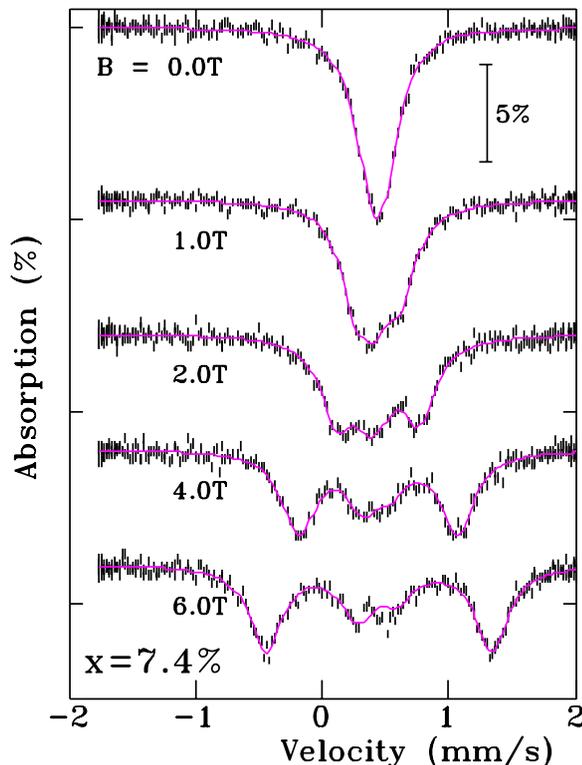


FIG. 2. Mössbauer spectra for a single-crystal mosaic of  $\text{Ba}(\text{Fe}_{0.926}\text{Co}_{0.074})_2\text{As}_2$  ( $x = 7.4\%$ ) at 5 K in several applied fields. The slight asymmetry in the spectra is due to an unresolved quadrupole contribution.

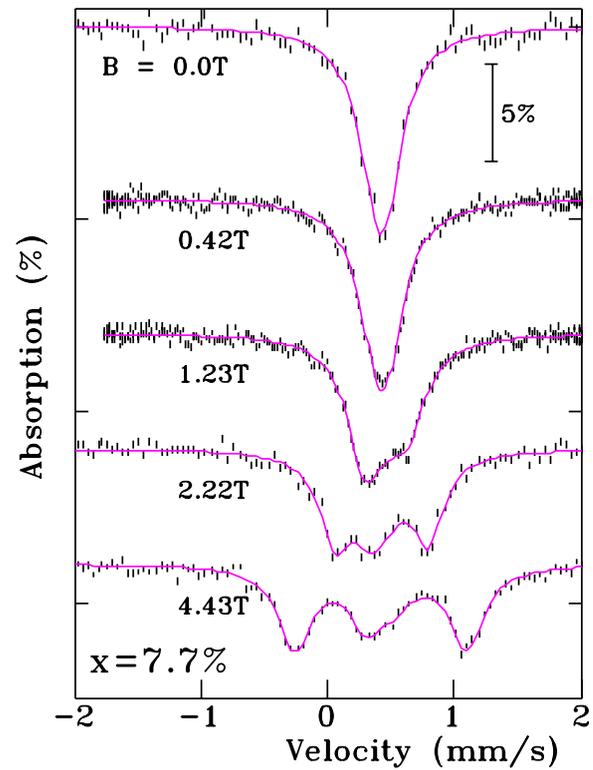


FIG. 3. Mössbauer spectra for a single-crystal mosaic of  $\text{Ba}(\text{Fe}_{0.923}\text{Co}_{0.077})_2\text{As}_2$  ( $x = 7.7\%$ ) at 5 K in several applied fields. The slight asymmetry in the spectra is due to an unresolved quadrupole contribution.

splitting of about  $0.05(1)$  mm/s, and the spectra had to be fitted using a solution to the full Hamiltonian to account for this effect. A comparable contribution is evident in the 5 K spectrum of the un-doped sample of  $\text{BaFe}_2\text{As}_2$  shown in Figure 1.

The observed hyperfine field ( $B_{hf}$ ) is plotted as a function of the applied field in Figure 4. A linear fit gives a slope of  $0.96(2)$  with an intercept  $-0.02(5)$  T, i.e., fully consistent with a line of slope 1 passing through the origin.

Two conclusions can be reached immediately. The first conclusion is that the applied field clearly penetrates the bulk

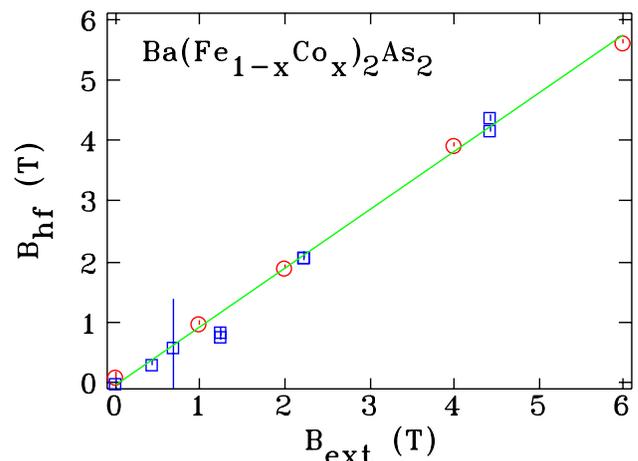


FIG. 4. Measured hyperfine fields ( $B_{hf}$ ) as a function of applied field for  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  with  $x = 7.4\%$  ( $\circ$ ) and  $7.7\%$  ( $\square$ ) at 5 K. The fitted line has a slope of  $0.96(2)$ , consistent with there being no induced field in either sample.

of the sample as we are unable to resolve any zero-field component. This is not surprising given the geometry (field applied perpendicular to the crystal sheets) and fields (many Tesla, much greater than  $\mu_0 H_{c1}$ ) used here. The sample is expected to be well into the vortex state with only a small fraction excluding the applied field.

The second conclusion is that there is no evidence for induced magnetic order. Antiferromagnetic ordering as seen in the parent  $\text{BaFe}_2\text{As}_2$ <sup>4,11,12</sup> would have many of the same effects as ferromagnetic ordering (with the obvious exception of a demagnetising field) but is unlikely to be induced by a uniform external field and will not be considered further. The hyperfine field associated with any field-induced ferromagnetic moment would lead either to a step offset (positive intercept in Figure 4) if the moment were induced by a small field, or some curvature if the moment were induced progressively and then saturated. The demagnetising field associated with ferromagnetic order would initially act to exclude the applied field, especially if the order were induced by a small applied field. This would shift the trend line in Figure 4 down but could not make the intercept negative as the iron hyperfine field is always much larger than the magnetisation, even in densely magnetic systems such as metallic iron where the ratio is more than 16. Here, with much of the volume occupied by non-magnetic barium and arsenic, the ratio would be much higher. A cancellation or compensation of these two contributions is not possible. Our fit to the data in Figure 4 is inconsistent with a positive offset from the origin and even the uncertainty of  $\sim 50$  mT puts the upper limit for an induced moment at less than 1% of that seen in the parent  $\text{BaFe}_2\text{As}_2$ , or much less than  $0.01 \mu_B/\text{Fe}$ .

The final possibility is that the induced moment is a linear function of the applied field, so that no curvature or offset occurs. As the hyperfine field at the iron nucleus is antiparallel to the local moment, the two contributions (from the local moment and the external field) act against each other and this could account for the slight (4(2)%) departure from unity in the fitted slope. If we scale the hyperfine field from the parent  $\text{BaFe}_2\text{As}_2$  where the moment ( $0.87 \mu_B$ )<sup>4</sup> and hyperfine field (5.5 T)<sup>7,11</sup> are both known, then the fitted slope puts a limit on the field-induced moment of  $6(3) \times 10^{-3} \mu_B/\text{T}$ .

The  $\mu\text{SR}$ -based studies that invoked field-induced magnetism to explain their observations all show a strong temperature dependence<sup>1-3</sup> with the effect disappearing near the superconducting transition. We checked for this in the  $x = 7.7\%$  sample at 2.22 T and 4.43 T by measuring at 5 K and 30 K (well above  $T_{sc}$  of  $\sim 21$  K) and found no significant difference. Indeed, while the measured hyperfine fields were consistent within error ( $\sim 30$  mT), in both cases, the fitted values were larger at 30 K than at 5 K, the reverse of the effect reported from  $\mu\text{SR}$  work.

#### IV. CONCLUSION

We studied single-crystal mosaics of self-flux grown  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  ( $x = 0\%$ , 4.4%, 7.4%, and 7.7%) in fields of up to 6 T applied parallel to the crystal  $c$ -axis and perpendicular to the crystal plates. In both superconducting compositions ( $x = 7.4\%$  and 7.7%), we observed complete penetration of the applied field, seeing only the applied field at the  $^{57}\text{Fe}$  nuclei with no shift that could be attributed to field-induced order. Furthermore, we observed no difference in the field at the  $^{57}\text{Fe}$  nuclei between 30 K (the normal state) and 5 K (where the samples were superconducting in zero field). Any field-induced magnetic ordering in superconducting  $\text{Ba}(\text{Fe}_{1-x}\text{Co}_x)_2\text{As}_2$  is certainly less than 1% of the order present in the parent  $\text{BaFe}_2\text{As}_2$ .

#### ACKNOWLEDGMENTS

Financial support for various stages of this work was provided by the Natural Sciences and Engineering Research Council of Canada and Fonds Québécois de la Recherche sur la Nature et les Technologies. J.M.C. acknowledges support from the University of New South Wales, Sydney, Australia. Work at the Ames Laboratory (P.C.C., S.L.B.) was supported by the Department of Energy, Basic Energy Sciences, Division of Materials Sciences and Engineering under Contract No. DE-AC02-07CH11358.

- <sup>1</sup>R. Khasanov, A. Maisuradze, H. Maeter, A. Kwadrin, H. Luetkens, A. Amato, W. Schnelle, H. Rosner, A. Leithe-Jasper, and H.-H. Klauss, *Phys. Rev. Lett.* **103**, 067010 (2009).
- <sup>2</sup>T. J. Williams, A. A. Aczel, E. Baggio-Saitovitch, S. L. Bud'ko, P. C. Canfield, J. P. Carlo, T. Goko, H. Kageyama, A. Kitada, J. Munevar, N. Ni, S. R. Saha, K. Kirschenbaum, J. Paglione, D. R. Sanchez-Candela, Y. J. Uemura, and G. M. Luke, *Phys. Rev. B* **82**, 094512 (2010).
- <sup>3</sup>J. E. Sonier, W. Huang, C. V. Kaiser, C. Cochran, V. Pacradouni, S. A. Sabok-Sayr, M. D. Lumsden, B. C. Sales, M. A. McGuire, A. S. Sefat, and D. Mandrus, *Phys. Rev. Lett.* **106**, 127002 (2011).
- <sup>4</sup>Q. Huang, Y. Qiu, W. Bao, M. A. Green, J. W. Lynn, Y. C. Gasparovic, T. Wu, G. Wu, and X. H. Chen, *Phys. Rev. Lett.* **101**, 257003 (2008).
- <sup>5</sup>S. Nandi, M. G. Kim, A. Kreyssig, R. M. Fernandes, D. K. Pratt, A. Thaler, N. Ni, S. L. Bud'ko, P. C. Canfield, J. Schmalian, R. J. McQueeney, and A. I. Goldman, *Phys. Rev. Lett.* **104**, 057006 (2010).
- <sup>6</sup>R. M. Fernandes, D. K. Pratt, W. Tian, J. Zarestky, A. Kreyssig, S. Nandi, M. G. Kim, A. Thaler, N. Ni, P. C. Canfield, R. J. McQueeney, J. Schmalian, and A. I. Goldman, *Phys. Rev. B* **81**, 140501 (2010).
- <sup>7</sup>P. Bonville, F. Rullier-Albenque, D. Colson, and A. Forget, *Europhys. Lett.* **89**, 67008 (2010).
- <sup>8</sup>N. Ni, M. E. Tillman, J.-Q. Yan, A. Kracher, S. T. Hannahs, S. L. Bud'ko, and P. C. Canfield, *Phys. Rev. B* **78**, 214515 (2008).
- <sup>9</sup>J.-H. Chu, J. G. Analytis, C. Kucharczyk, and I. R. Fisher, *Phys. Rev. B* **79**, 014506 (2009).
- <sup>10</sup>C. Lester, J.-H. Chu, J. G. Analytis, S. C. Capelli, A. S. Erickson, C. L. Condon, M. F. Toney, I. R. Fisher, and S. M. Hayden, *Phys. Rev. B* **79**, 144523 (2009).
- <sup>11</sup>M. Rotter, M. Tegel, D. Johrendt, I. Schellenberg, W. Hermes, and R. Pöttgen, *Phys. Rev. B* **78**, 020503 (2008).
- <sup>12</sup>S. D. Wilson, Z. Yamani, C. R. Rotundu, B. Freelon, E. Bourret-Courchesne, and R. J. Birgeneau, *Phys. Rev. B* **79**, 184519 (2009).