

2002

# The Intermetallic Compound BaAuSb

Eun Kwang Lee  
*Chungnam National University*

Gordon J. Miller  
*Iowa State University, gmiller@iastate.edu*

Sung Kwon Kang  
*Chungnam National University*

Follow this and additional works at: [http://lib.dr.iastate.edu/chem\\_pubs](http://lib.dr.iastate.edu/chem_pubs)

 Part of the [Materials Chemistry Commons](#), [Other Chemistry Commons](#), and the [Physical Chemistry Commons](#)

The complete bibliographic information for this item can be found at [http://lib.dr.iastate.edu/chem\\_pubs/847](http://lib.dr.iastate.edu/chem_pubs/847). For information on how to cite this item, please visit <http://lib.dr.iastate.edu/howtocite.html>.

---

This Article is brought to you for free and open access by the Chemistry at Iowa State University Digital Repository. It has been accepted for inclusion in Chemistry Publications by an authorized administrator of Iowa State University Digital Repository. For more information, please contact [digirep@iastate.edu](mailto:digirep@iastate.edu).

---

# The Intermetallic Compound BaAuSb

## Abstract

The title compound was obtained as a by-product when elemental Ba [rod, Aesar (99.99%)], Au [powder, 100 mesh, Aesar (99.999%)], and Sb [powder, 100 mesh, Aesar (99.999%)] were loaded into a tantalum tube (Nobel-Met. Ltd, >99.85%, 0.375 OD) in a 1:1:2 molar ratio in an Ar-filled glove-box. The tube was sealed in an arc-melter under argon, and heated to 973 K for 3 d in a fused-silica jacket. The reaction container was cooled slowly to 673 K at 10 K h<sup>-1</sup>, and then quenched to room temperature. When the tantalum tube was opened in the Ar-filled glove-box, gray irregular-shaped crystals of the title compound were found in the product. Suitable single crystals were mounted in 0.3 mm thin-walled capillaries for subsequent diffraction experiments.

## Disciplines

Materials Chemistry | Other Chemistry | Physical Chemistry

## Comments

This article is from *Acta Crystallographica Section E* 58 (2002): i17, doi:10.1107/S1600536802000569. Posted with permission.

## The intermetallic compound BaAuSb

Eun Kwang Lee,<sup>a</sup> Gordon J. Miller<sup>b</sup> and Sung Kwon Kang<sup>a\*</sup><sup>a</sup>Department of Chemistry, Chungnam National University, Daejeon 305-764, South Korea, and<sup>b</sup>Department of Chemistry, Iowa State University, Ames, IA 50011, USA

Correspondence e-mail: skkang@cnu.ac.kr

## Key indicators

Single-crystal X-ray study

T = 293 K

Mean  $\sigma(\text{Ba-Sb}) = 0.0003 \text{ \AA}$ 

R factor = 0.033

wR factor = 0.082

Data-to-parameter ratio = 11.1

For details of how these key indicators were automatically derived from the article, see <http://journals.iucr.org/e>.

The title compound, barium gold antimonide, BaAuSb, is isostructural with ZrBeSi, which adopts the space group  $P6_3/mmc$ . The Au and Sb atoms form planar honeycomb layers, with an Au–Sb distance of 2.7402 (3) Å.

## Comment

During studies on the ternary barium–gold–antimony system using sealed tantalum containers for their preparation, the intermetallic compound, BaAuSb, was obtained as a side product. Previously, this compound was prepared by direct reaction with stoichiometric amounts of the components and characterized by X-ray powder diffraction (Merlo & Fornasini, 1990).

BaAuSb is isostructural with ZrBeSi, a ternary ordered variant of the binary type  $\text{Ni}_2\text{In}$  (Vogel & Schuster, 1980). Au and Sb form planar hexagonal sheets like graphite, with Au and Sb alternating in the layer. Ba atoms lie between two layers and are positioned over the centers of the hexagonal rings. The shortest interatomic distance, Au–Sb, is 2.7402 (3) Å, and each Ba atom is bonded to six Au and six Sb atoms at distances of 3.5948 (3) Å.

## Experimental

The title compound was obtained as a by-product when elemental Ba [rod, Aesar (99.99%)], Au [powder, 100 mesh, Aesar (99.999%)], and Sb [powder, 100 mesh, Aesar (99.999%)] were loaded into a tantalum tube (Nobel-Met. Ltd, >99.85%, 0.375 OD) in a 1:1:2 molar ratio in an

Received 2 January 2002

Accepted 9 January 2002

Online 18 January 2002

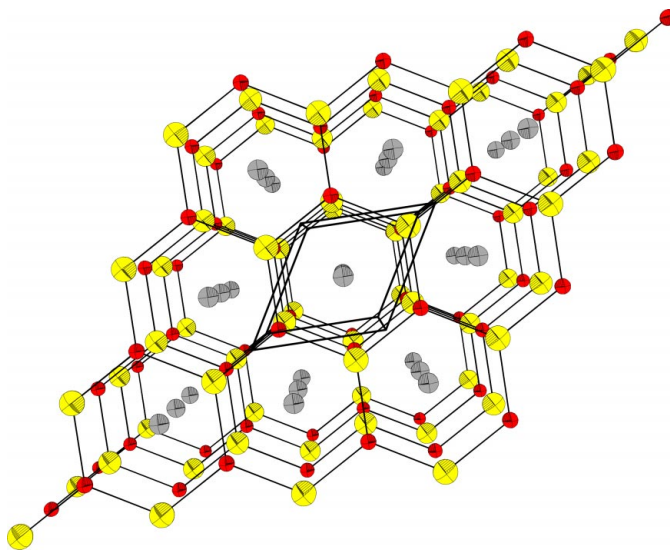


Figure 1

An (001) perspective projection of BaAuSb. Displacement ellipsoids are drawn at the 99% probability level. Key: Ba gray, Au gold and Sb red.

Ar-filled glove-box. The tube was sealed in an arc-melter under argon, and heated to 973 K for 3 d in a fused-silica jacket. The reaction container was cooled slowly to 673 K at 10 K h<sup>-1</sup>, and then quenched to room temperature. When the tantalum tube was opened in the Ar-filled glove-box, gray irregular-shaped crystals of the title compound were found in the product. Suitable single crystals were mounted in 0.3 mm thin-walled capillaries for subsequent diffraction experiments.

## Crystal data

BaAuSb  
 $M_r = 456.06$   
 Hexagonal,  $P6_3/mmc$   
 $a = 4.7461$  (6) Å  
 $c = 9.3075$  (11) Å  
 $V = 181.57$  (4) Å<sup>3</sup>  
 $Z = 2$   
 $D_x = 8.342$  Mg m<sup>-3</sup>

Mo  $K\alpha$  radiation  
 Cell parameters from 48 reflections  
 $\theta = 4.4$ – $14.0^\circ$   
 $\mu = 58.13$  mm<sup>-1</sup>  
 $T = 293$  (2) K  
 Irregular, gray  
 $0.10 \times 0.05 \times 0.05$  mm

## Data collection

Bruker P4 diffractometer  
 $2\theta/\omega$  scans  
 Absorption correction:  $\psi$  scan  
 (North *et al.*, 1968)  
 $T_{\min} = 0.030$ ,  $T_{\max} = 0.055$   
 412 measured reflections  
 89 independent reflections  
 78 reflections with  $I > 2\sigma(I)$

$R_{\text{int}} = 0.075$   
 $\theta_{\text{max}} = 25.9^\circ$   
 $h = -1 \rightarrow 5$   
 $k = -5 \rightarrow 1$   
 $l = -11 \rightarrow 1$   
 3 standard reflections  
 every 97 reflections  
 intensity decay: none

## Refinement

Refinement on  $F^2$   
 $R[F^2 > 2\sigma(F^2)] = 0.033$   
 $wR(F^2) = 0.082$   
 $S = 1.14$   
 89 reflections  
 8 parameters

$w = 1/[\sigma^2(F_o^2) + (0.0422P)^2]$   
 where  $P = (F_o^2 + 2F_c^2)/3$   
 $(\Delta/\sigma)_{\text{max}} < 0.001$   
 $\Delta\rho_{\text{max}} = 1.74$  e Å<sup>-3</sup>  
 $\Delta\rho_{\text{min}} = -2.04$  e Å<sup>-3</sup>  
 Extinction correction: *SHELXL97*  
 Extinction coefficient: 0.028 (3)

Space groups  $P\bar{3}1c$ ,  $P31c$ ,  $P6_3mc$ ,  $P6_3/mmc$ , and  $P\bar{6}2c$  were allowed based upon the observed systematic absences. Space group  $P6_3/mmc$  was selected for initial refinements, and this group was confirmed by comparing the refinement results using the other four groups. Ba, Au, and Sb atoms were readily located from an  $E$  map, and refined with anisotropic displacement parameters. The largest residuals in the final difference map were 1.74 e Å<sup>-3</sup> at a distance of 0.42 Å from Ba and  $-2.04$  e Å<sup>-3</sup> at a distance of 1.30 Å from the Au atom. All atoms lie in special positions with no refined coordinates.

Data collection: *XSCANS* (Bruker, 1996); cell refinement: *XSCANS*; data reduction: *SHELXTL* (Bruker, 1997); program(s) used to solve structure: *SHELXS97* (Sheldrick, 1997); program(s) used to refine structure: *SHELXL97* (Sheldrick, 1997); software used to prepare material for publication: *WinGX* (Farrugia, 1999).

The authors wish to acknowledge the financial support of the Korean Research Foundation made in the program year of 2000 (project No. DP0222).

## References

- Bruker (1997). *SHELXTL*. Version 5.1. Bruker AXS Inc., Madison, Wisconsin, USA.  
 Farrugia, L. J. (1999). *J. Appl. Cryst.* **32**, 837–838.  
 Merlo, F. & Fornasini, M. L. (1990). *J. Less Common Met.* **166**, 319–327.  
 North, A. C. T., Phillips, D. C. & Mathews, F. S. (1968). *Acta Cryst.* **A24**, 351–359.  
 Sheldrick, G. M. (1997). *SHELXL97* and *SHELXS97*. University of Göttingen, Germany.  
 Siemens (1996). *XSCANS*. Version 2.2. Siemens Analytical X-ray Instruments Inc., Madison, Wisconsin, USA.  
 Vogel, R. & Schuster, H. U. (1980). *Z. Naturforsch. Teil B*, **35**, 114–116.